



UNIVERSITY  
OF WOLLONGONG  
AUSTRALIA

University of Wollongong  
Research Online

---

Coal Operators' Conference

Faculty of Engineering and Information Sciences

---

2008

# Development of a Site Specific Self-Heating Rate Prediction Equation for a High Volatile Bituminous Coal

B. B. Beamish  
*University of Queensland*

W. Sainsbury  
*University of Queensland*

---

## Publication Details

This conference paper was originally published as Beamish, BB and Sainsbury, W, Development of a Site Specific Self-Heating Rate Prediction Equation for a High Volatile Bituminous Coal in Aziz, N (ed), Coal 2008: Coal Operators' Conference, University of Wollongong & the Australasian Institute of Mining and Metallurgy, 2008, 161-165.

Research Online is the open access institutional repository for the University of Wollongong. For further information contact the UOW Library:  
[research-pubs@uow.edu.au](mailto:research-pubs@uow.edu.au)

# DEVELOPMENT OF A SITE SPECIFIC SELF-HEATING RATE PREDICTION EQUATION FOR A HIGH VOLATILE BITUMINOUS COAL

**B Basil Beamish<sup>1</sup> and Wade Sainsbury<sup>1</sup>**

**ABSTRACT:** The  $R_{70}$  test was performed on a series of coal samples taken from different locations in a US longwall mine. The values obtained produced a definite relationship between  $R_{70}$  and ash content, with the exception of one anomalously low result. An ash analysis of the sample showed that it had a high sodium ( $\text{Na}_2\text{O}$ ) content in response to the presence of the sodium zeolite mineral, analcime. A multiple regression of the  $R_{70}$ , ash content and sodium ( $\text{Na}_2\text{O}$ ) content of the samples produced a self-heating rate prediction equation with an  $R^2$  of 0.98. This equation can now be used to predict the  $R_{70}$  self-heating rate of the coal at any location throughout the mine, thus assisting with hazard management planning.

## INTRODUCTION

Low-temperature oxidation of coal results in an exothermic reaction and without sufficient dispersion of the heat generated will eventually result in spontaneous combustion. This unwanted outcome can cause huge losses in revenue and more importantly, cause major problems with safety. In underground mining operations the combination of in-seam gas, inappropriate ventilation networks and self-heating areas of coal can equate to a catastrophic disaster. Examples of these events in Australia are recorded by Ham (2005).

The parameters that control a coal's propensity for self-heating have been the subject of many investigations. Relationships between coal properties and self-heating indices have been published in a number of studies (Humphreys, Rowlands and Cudmore, 1981; Moxon and Richardson, 1985; Singh and Demirbilek, 1987; Barve and Mahadevan, 1994; Beamish, Barakat and St. George, 2000, 2001). Humphreys, Rowlands and Cudmore (1981) found a simple relationship between the coal self-heating index parameter,  $R_{70}$  and coal rank. However, research by Beamish, Barakat and St. George (2001) and Beamish (2005) on New Zealand and Australian coals covering a wider range of coal ranks showed that the  $R_{70}$  coal self-heating rate relationship with rank is non-linear. Beamish and Blazak (2005) also showed that  $R_{70}$  values decrease significantly with increasing mineral matter content, as defined by the ash content of the coal.

This paper presents the development of a site specific equation used for the prediction of  $R_{70}$  self-heating rate of a high volatile bituminous coal that is being mined by longwall methods in the United States (US). The site specific nature of coal self-heating has been identified by earlier work on Australian coals using the  $R_{70}$  test procedure (Beamish *et al.*, 2005; Beamish and Clarkson, 2006). However, this is the first time that the  $R_{70}$  test procedure has been applied to US coals.

## EXPERIMENTAL PROCEDURE

### Coal samples

The coal samples used for test work were collected from the workings of an operating longwall coal mine in the United States. These samples were sent to The University of Queensland's Spontaneous Combustion Testing Laboratory, with each of the coal lumps individually wrapped in cling wrap, and stored in an air-tight sealed bag that was placed in the laboratory freezer until the commencement of testing.

### R70 Test Procedure

The full adiabatic oven testing procedure is outlined in (Beamish, Barakat and St George, 2000). In preparation for the test, the coal samples are taken out of the freezer and allowed to thaw for one hour. Once the samples are thawed they are crushed and sieved to achieve a particle size of  $< 212 \mu\text{m}$ . This process is to be completed in as little time as possible to reduce oxidation on the fresh surface of the coal. The  $R_{70}$  test is carried out on a dry basis therefore all the samples are dried. 150 g of the sample is placed in a 750mL flask then in the drying oven and all the oxygen removed. The sample is kept in the oven with a constant nitrogen flow of 250 mL/min. Then it is heated to  $110^\circ\text{C}$  and left to dry for 16 hours.

After the drying process is complete, the sample is transferred to the 450 mL reaction vessel and placed in the adiabatic oven. Here it is allowed to stabilise at  $40^\circ\text{C}$  in a nitrogen-rich atmosphere. Once this was achieved,

<sup>1</sup> School of Engineering, The University of Queensland

oxygen is then supplied to the coal at a rate of 50mL/min. For the duration of the test, the oven is put on remote monitoring where the change in temperature of the coal is followed by the oven to minimise any heat losses from the system and the data is recorded by a computer logging system. Once the coal temperature reaches 160°C, the supply of oxygen is cut off and the oven heating elements are disengaged. The sample is then allowed to cool before being removed and the equipment cleaned and prepared for the next test.

## RESULTS AND DISCUSSION

### R70 Results and Ash Content Relationship

Adiabatic self-heating curves for each of the seven samples tested are shown in Figure 1. The R70 value is determined as the average self-heating rate from the starting temperature (~40°C) till the coal reaches 70°C and is expressed in units of °C/h. A plot of the R70 values against their respective ash contents is shown in Figure 2. There is a strong linear relationship evident for six of the seven samples with an R2 value of 0.97. As described by Beamish and Blazak (2005), generally as the ash content increases for a given rank of coal the R70 value decreases. In earlier work this has been attributed to the mineral matter in the coal acting as a heat sink (Humphreys, Rowlands and Cudmore, 1981; Smith, Miron and Lazzara, 1988) and thus lowering the self-heating rate of the coal. However, more recent work by Beamish and Arisoy (2008) points to the possibility of other physico-chemical mechanisms causing the decrease in self-heating rate of the coal. The slope of the relationship shown in Figure 2 is much steeper than those presented by Beamish et al. (2005) and Beamish and Clarkson (2006) for Australian high volatile bituminous coals. This steep slope is not consistent with a simple heat sink effect.

Sample 6A appears to be an outlier compared to the rest of the samples tested. This cannot be attributed to repeatability error, as samples 3A and 3B have the same ash content (6.5%) and produced R70 values of 3.09 and 3.01°C/h respectively. These values are well within the normal repeatability limits for testing of ±5%.

One possible explanation for the dramatic decrease in self-heating rate for this sample could be a difference in coal type due to a change in maceral composition. However, a Suggate rank plot (Suggate, 1998 and 2000) of the samples showed no variation in coal type between them. The only possibility left is that there is a different mineral composition present in this sample that is causing the decrease in R70.

### Ash Analysis

In an effort to explain the variance observed in the R70 result obtained for sample 6A an ash analysis was conducted to identify possible mineralogical associations. The ash analysis uses a wavelength dispersive x-ray fluorescence spectrometric method which can determine concentrations of silicon, aluminium, iron, calcium, magnesium, sodium, potassium, titanium, manganese, phosphorous, sulphur, strontium, barium, zinc and vanadium.

A duplicate of each sample of coal was sent to a registered laboratory for ash analysis according to the relevant Australian Standards (AS1038.3 2000 and AS1038.14.3 1999). The results from the seven different samples have been collated in Table 1. Each sample was tested for the presence of 15 standard elements and is displayed as a percentage dry basis in oxide form.

The most striking feature about the ash analysis results for sample 6A (Table 1) is the very high sodium content (10%). This is at least three times the levels of the other samples. Having obtained this possible link to the cause of the low R70 value for the sample, the next step was to identify the mineral responsible for the sodium. A sample of the coal was analysed using X-Ray Diffraction (XRD) and the results obtained showed the presence of the sodium zeolite mineral, analcime (NaAlSi<sub>2</sub>O<sub>6</sub>·H<sub>2</sub>O). Initial scanning electron microscopy analysis has confirmed this and low temperature ashing of the sample is still in progress to establish any other mineral assemblage associations. The results of this additional work will be published at a later date, including a possible genesis for the presence of the analcime.

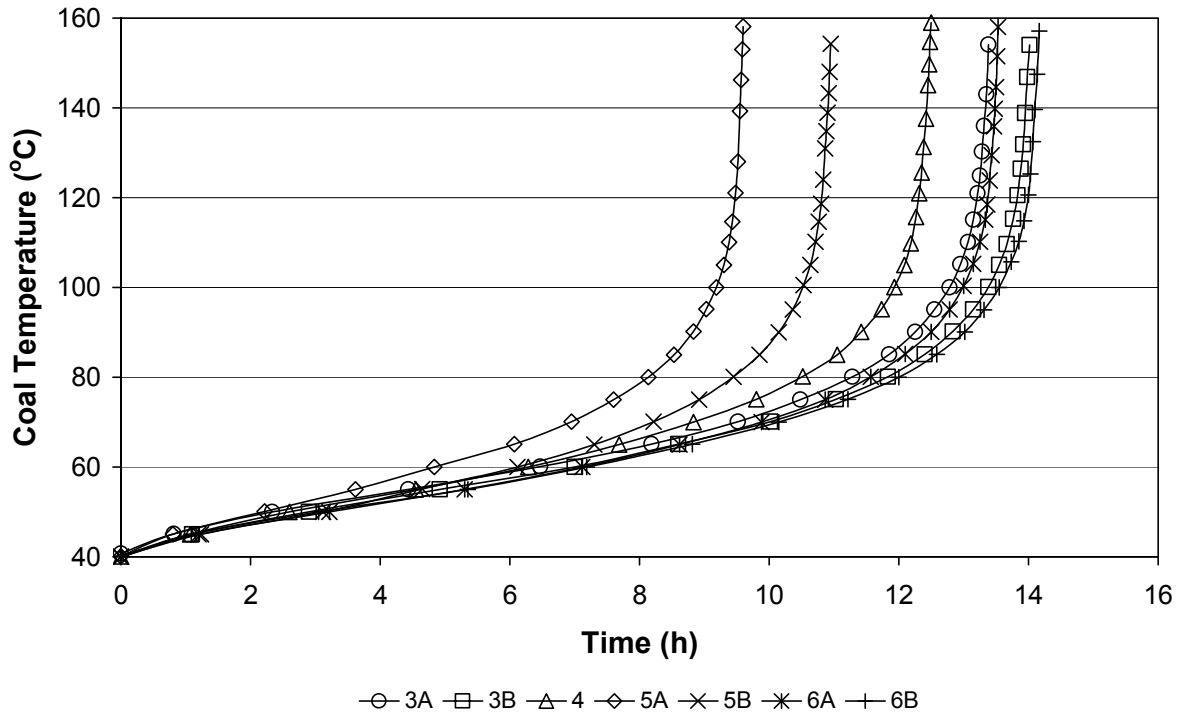


Figure 1 - Adiabatic self-heating curves for a high volatile bituminous coal

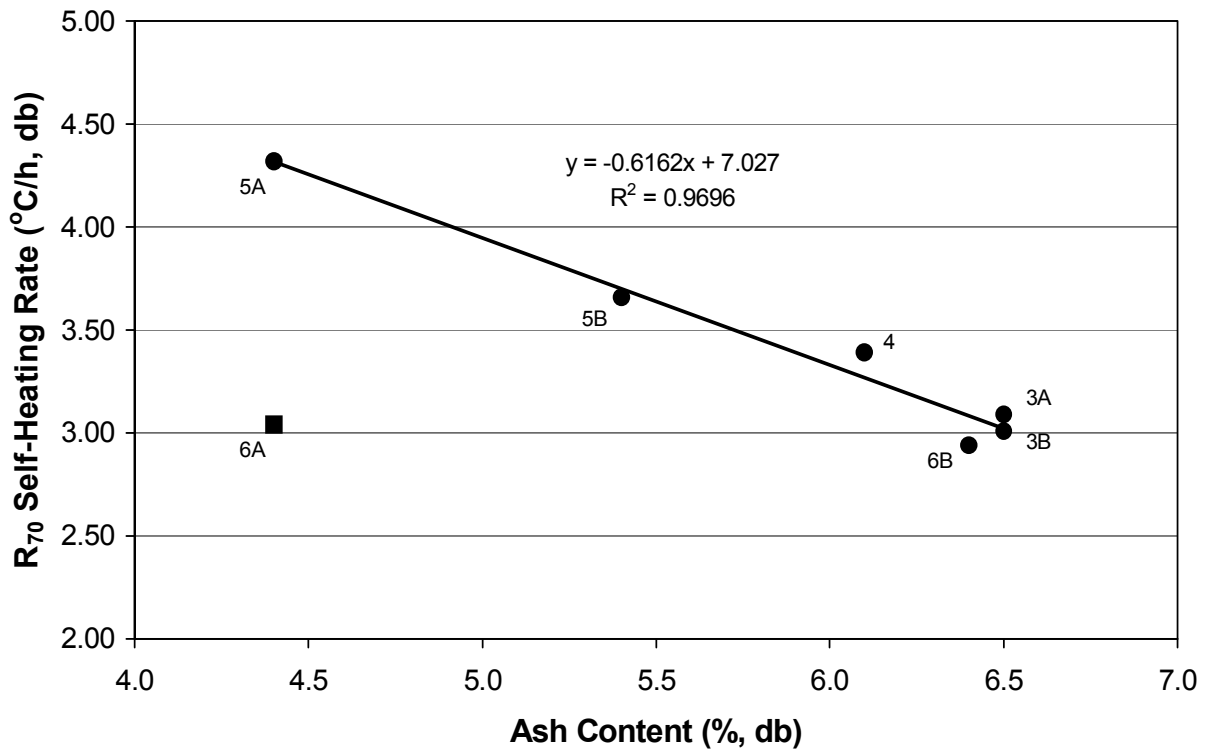


Figure 2 - Relationship between R<sub>70</sub> self-heating rate and ash content

Table 1 - Ash Analysis Results

Ash Composition (% db)	3A	3B	4	5A	5B	6A	6B
Silicon (SiO <sub>2</sub> )	56.0	56.7	70.0	49.0	53.0	50.5	54.5
Aluminium (Al <sub>2</sub> O <sub>3</sub> )	30.2	31.0	18.1	28.0	27.0	25.5	23.5
Iron (Fe <sub>2</sub> O <sub>3</sub> )	4.6	4.8	4.7	8.3	5.4	5.2	4.0
Calcium (CaO)	0.8	0.82	1.2	4.5	4.1	4.0	4.9
Magnesium (MgO)	1.2	1.2	1.0	1.9	1.5	1.3	1.3
Sodium (Na <sub>2</sub> O)	2.7	3.0	1.6	3.4	2.5	10.0	3.5
Potassium (K <sub>2</sub> O)	0.47	0.48	0.41	0.47	0.63	0.44	0.38
Titanium (TiO <sub>2</sub> )	1.5	1.7	1.7	1.4	1.4	1.4	1.7
Manganese (Mn <sub>3</sub> O <sub>4</sub> )	0.02	0.01	0.02	0.03	0.01	0.01	0.01
Phosphorous (P <sub>2</sub> O <sub>5</sub> )	0.14	0.15	0.12	0.56	1.50	1.10	1.00
Sulphur (SO <sub>3</sub> )	0.61	0.43	0.8	2.6	2.7	1.9	3.5
Strontium (SrO)	0.50	0.35	0.30	0.40	0.19	0.51	0.01
Barium (BaO)	0.35	0.35	0.30	0.30	0.34	0.45	0.23
Zinc (ZnO)	0.02	0.02	0.02	0.02	0.02	0.02	0.02
Vanadium (V <sub>2</sub> O <sub>5</sub> )	0.02	0.02	0.03	0.02	0.02	0.01	0.02

#### Multiple regression analysis

There appears to be two dominant factors affecting the R<sub>70</sub> self-heating rate values of these samples, ash content and the amount of sodium present in the ash. To determine the influence these parameters are having a multiple regression analysis was performed with the R<sub>70</sub> value as the dependent factor. The regression equation obtained is:

$$R_{70} (\text{°C/h}) = -0.6351 \times \text{Ash} - 0.1767 \times \text{Na}_2\text{O} + 7.63$$

$$(R^2 = 0.98)$$

where, both Ash and Na<sub>2</sub>O are in dry weight percent.

A comparison of the actual and predicted self-heating rates found that only a minor variance existed between the two values. The confidence of this equation is currently average, however a larger dataset would allow a much more precise equation to be created. Table 2 contains the calculated residual values for each of the samples. It can be seen that the difference ranges from 0.003 to 0.095 °C/h, which is extremely low and well within the repeatability limits of the test. Therefore, this equation can be used throughout the mine with an acceptable degree of confidence for predicting the R<sub>70</sub> self-heating rate of the coal.

Table 2 - Comparison Actual and Predicted R70

Sample	Actual R <sub>70</sub> (°C/h)	Predicted R <sub>70</sub> (°C/h)	Residual (°C/h)
3A	3.09	3.02	0.069
3B	3.01	2.96	0.042
4	3.39	3.46	0.079
5A	4.32	4.23	0.089
5B	3.66	3.75	0.095
6A	3.04	3.06	0.025
6B	2.94	2.94	0.003

## CONCLUSIONS

Adiabatic testing has been performed on a series of high volatile bituminous coal samples taken from different locations through an underground longwall mining operation. The values obtained produced a definite linear relationship between  $R_{70}$  and ash content. A simple heat sink effect mechanism is not evident as the decreasing self-heating rate trend for the samples is much too steep for this.

An ash analysis of the coal provided a quantitative breakdown of the major inorganic constituents within the samples. These results showed a strong negative association with sodium ( $\text{Na}_2\text{O}$ ) in one of the samples which did not conform to the observed simple linear  $R_{70}$  and ash content relationship. The sodium in the sample is linked to the presence of the mineral analcime, which may be acting as a natural inhibitor to the coal oxidation process and thus reducing the self-heating rate.

A multiple regression of the  $R_{70}$ , ash content and sodium ( $\text{Na}_2\text{O}$ ) content produced a self-heating rate prediction equation with an  $R^2$  of 0.98. Similar site specific relationships are being developed for other mines throughout Australia and overseas, which can be used to assist with the mine's hazard management planning.

## ACKNOWLEDGEMENTS

The authors would like to thank mine site personnel for providing an excellent range of samples to be tested. The mine name has been withheld for confidentiality reasons. UniQuest Ltd and Simtars are also thanked for granting permission to publish these results.

## REFERENCES

- Barve, S D and Mahadevan, V, 1994. Prediction of spontaneous heating liability of Indian coals based on proximate constituents, in Proceedings 12th International Coal Preparation Congress, pp557-562, Cracow, Poland.
- Beamish, B B, 2005. Comparison of the  $R_{70}$  self-heating rate of New Zealand and Australian coals to Suggate rank parameter, *International Journal of Coal Geology*, 64(1-2):139-144.
- Beamish, B B and Arisoy, A, 2008. Effect of mineral matter on coal self-heating rate, *Fuel*, 87:125-130.
- Beamish, B B and Blazak, D G, 2005. Relationship between ash content and  $R_{70}$  self-heating rate of Callide Coal, *International Journal of Coal Geology*, 64(1-2):126-132.
- Beamish, B B and Clarkson, F. Self-heating rates of Sydney Basin coals – The emerging picture, in Proceedings of the 36th Sydney Basin Symposium, pp1-8, University of Wollongong.
- Beamish, B B, Barakat, M A and St George, J D, 2001. Spontaneous-combustion propensity of New Zealand coals under adiabatic conditions, *International Journal of Coal Geology*, 45:217-224.
- Beamish, B B, Barakat, D G and St George, J D, 2000. Adiabatic testing procedures for determining the self-heating propensity of coal and sample ageing effects, *Thermochimica Acta*, 362(1-2): 79-87.
- Beamish, B B, Blazak, D G, Hogarth, L C S and Jabouri, I, 2005.  $R_{70}$  relationships and their interpretation at a mine site, in Proceedings of the 6th Australasian Coal Operators' Conference, pp183-185, The AusIMM, Melbourne, Australia.
- Ham, B, 2005. A review of spontaneous combustion incidents, in Proceedings of the 6th Australasian Coal Operators' Conference, pp237-242, The AusIMM, Melbourne, Australia.
- Humphreys, D, Rowlands, D and Cudmore, J F, 1981. Spontaneous combustion of some Queensland coals, in Proceedings Ignitions, Explosions and Fires in Coal Mines Symposium, pp5-1 – 5-19, The AusIMM Illawarra Branch, Melbourne, Australia.
- Moxon, N T and Richardson, S B, 1985. Development of a self-heating index for coal, *Coal Preparation*, 2:91-105.
- Singh, R N and Demirbilek, S, 1987. Statistical appraisal of intrinsic factors affecting spontaneous combustion of coal, *Mining Science and Technology*, 4:155-165.
- Smith, A C, Miron, Y and Lazzara, P, 1988. Inhibition of spontaneous combustion of coal, US Bureau of Mines Report of Investigation, RI 9196.
- Standards Australia International 1999, *Coal and Coke - Analysis and Testing – Part 14.3: High rank coal ash and coke ash – Major and minor elements – Wavelength dispersive x-ray fluorescence method*, AS1038.14.3-1999, Standards Australia International, Australia.
- Standards Australia International 2000, *Coal and Coke - Analysis and Testing – Proximate analysis of higher rank coal*, AS1038.3-2000, Standards Australia International, Australia.
- Suggate, R P, 2000. The Rank (Sr) scale: its basis and its application as a maturity index for all coals, *New Zealand Journal of Geology and Geophysics*, 43:521-553.
- Suggate, R P, 1998. Analytical variation in Australian coals related to coal type and rank, *International Journal of Coal Geology*, 37:179-206.