

*Faculty of Engineering*  
*Faculty of Engineering - Papers*

---

*University of Wollongong*

*Year 2003*

---

A comparison of Ag and Ag-alloy  
sheathed Bi-2223 tapes

H. K. Liu\*      Z. M. Zhang<sup>†</sup>      R. Zeng<sup>‡</sup>  
J. Horvat\*\*      M. Apperley<sup>††</sup>

\*University of Wollongong, hua@uow.edu.au

<sup>†</sup>University of Wollongong

<sup>‡</sup>University of Wollongong

\*\*University of Wollongong, jhorvat@uow.edu.au

<sup>††</sup>Australian Superconductors, Coniston

This article was originally published as: Liu, HK, Zhang, ZM, Zeng, R et al, A comparison of Ag and Ag-alloy sheathed Bi-2223 tapes, IEEE Transactions on Applied Superconductivity, June 2003, 13(2)3, 3004-3007. Copyright IEEE 2003.

This paper is posted at Research Online.

<http://ro.uow.edu.au/engpapers/37>

# A Comparison of Ag and Ag-Alloy Sheathed Bi-2223 Tapes

Hua K. Liu, Zhong M. Zhang, Rong Zeng, Josip Horvat, and Miles Apperley

**Abstract**—Ag and Ag-alloy sheathed Bi-2223 tapes were fabricated by a powder-in-tube technique with different configurations of the precursor and restack sheath materials: Ag, AgAu7 wt%, AgSb0.6 wt%, AgMg0.2 wt%. Analysis of the  $I_c$  and volume fractions of the Bi-2223, Bi-2212, Bi-2201 and Bi-3221 phases indicated that volume fractions of Bi-2223 > 90%, Bi-2212 ~ 5%, Bi-2201 ~ 0% and Bi-3221 < 2%, normally result in tapes with the highest  $I_c$ . The mechanical properties of the tapes revealed consistent results. Generally, the harder the sheath material, the higher tolerance to the bending strain and higher the tensile strength of the tape. The sequence of the alloys' hardness from highest to lowest was AgMg0.2 wt%, AgSb0.6 wt%, AgAu7 wt% or Ag.

**Index Terms**—Ag and Ag-alloy sheath, Bi-2223 tapes, mechanical properties, phase volume fractions.

## I. INTRODUCTION

MANY groups [1]–[12] have investigated Ag and Ag alloys (including elements Au, Mg, Pd, Mn, Cu, Ni, and Ti) as the sheath materials for fabricating  $(\text{Bi,Pb})_2\text{Sr}_2\text{Ca}_2\text{Cu}_3\text{O}_{10-x}$  (Bi-2223) tapes suitable for applications such as power cables, current leads, and coils for transformers and motors. The Bi-2223 material is a brittle ceramic, so the sheath material must provide a strengthening mechanism for the filaments without diminishing the properties of the Bi-2223 during processing. In this paper we report the results for the tapes fabricated by a powder-in-tube technique with different configurations of Ag, AgAu7 wt% AgSb0.6 wt% and AgMg0.2 wt% as the precursor and restack sheath materials.

## II. EXPERIMENTAL

Ag and Ag-alloy sheathed tapes with 37 filaments were fabricated using commercial Bi-2223 precursor material and powder-in-tube techniques. The sheath configurations of the tapes are listed in Table I.

Short length samples of tape were heat treated at a temperature in the range of 832 °C to 846 °C for the first stage (HT1), followed by a second stage (HT2: 825 °C for 40 h, slow cooled

TABLE I  
37 FILAMENT BI-2223 TAPE CONFIGURATIONS

Tape number	Restack sheath	Precursor sheath
1	Ag	Ag
2	AgAu7wt%	AgAu7wt%
3	AgSb0.6wt%	Ag
4	AgAu7wt%	AgSb0.6wt%
5	AgSb0.6wt%	AgAu7wt%
6	AgMg0.2wt%	AgAu7wt%
7	Ag	AgSb0.6wt%

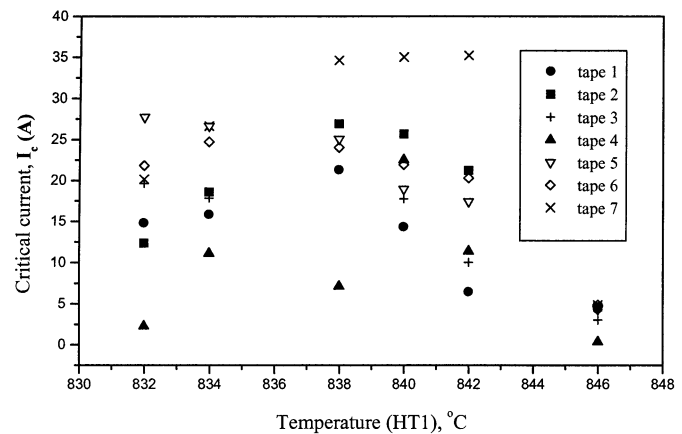


Fig. 1. Critical current ( $I_c$ ) of short tapes measured at 77 K and self-field after HT2.

to 785 °C and then normal cooled to room temperature). An intermediate roll (IR) pass was performed between each heat treatment stage.

The phase compositions were determined from X-ray diffraction data. Assuming:  $a$  %Bi-2223 +  $b$  %Bi-2212 +  $c$  %Bi-2201 +  $d$  %Bi-3221 = 100%, the volume fractions of the phases were calculated by the peak intensity ( $I_{2223}(0010)$ ,  $I_{2212}(008)$ ,  $I_{2201}(006)$ , and  $I_{3221}(300)$ ) of Bi-2223, Bi-2212, Bi-2201 and Bi-3221 phases, respectively, divided by the sum of their intensities.

The critical current ( $I_c$ ) was measured in self-field at 77 K using a four-probe method and a  $1 \mu\text{V}/\text{cm}$  criterion. The critical current density ( $J_c$ ) vs. magnetic field ( $H$ ) of the tapes was determined at 77 K in the directions of  $H \perp c$  ( $H//ab$ ) and  $H//c$ .

The bend strain tolerance was investigated by measuring the critical current at zero field ( $I_{c0}$ ) of a short sample and the  $I_c$  after one-way bending the sample around progressively smaller diameter formers in the range 110 to 20 mm. The sample was straightened after each bend cycle. The percentage of bend

Manuscript received August 6, 2002. This work was supported by the Australian Research Council, Department of Education, Training and Youth Affairs, and Australian Superconductors Ltd.

H. K. Liu, Z. M. Zhang, R. Zeng, and J. Horvat are with the Institute for Superconducting and Electronic Materials (ISEM), University of Wollongong, Wollongong, NSW 2522 Australia (e-mail: hua\_liu@uow.edu.au; zhongmin@uow.edu.au; rzeng@uow.edu.au; jhorvat@uow.edu.au).

M. Apperley is with the Australian Superconductors, Engineering and Innovation Education Centre, Miller St., Coniston, NSW 2500, Australia (e-mail: htsdev@ozemail.com.au)

Digital Object Identifier 10.1109/TASC.2003.812052

TABLE II  
PHASES CONTENT (%) FROM X-RAY (HT 1: 834 °C).

	Tape 1		Tape 2		Tape 3		Tape 4		Tape 5		Tape 6		Tape 7	
	HT 1	HT 2	HT 1	HT 2	HT 1	HT 2	HT 1	HT 2	HT 1	HT 2	HT 1	HT 2	HT 1	HT 2
Bi-2223	82.0	91.7	80.6	82.6	82.6	82.5	83.3	81.0	77.5	91.7	83.3	84.0	82.6	94.3
Bi-2212	12.3	5.5	12.1	11.6	13.2	11.7	13.3	14.0	18.6	4.6	14.2	10.1	9.9	4.7
Bi-2201	1.6	~0	1.6	~0	2.5	~0	2.5	0.8	~0	~0	0.8	~0	2.5	~0
Bi-3221	2.5	5.5	4.0	4.1	0.8	4.9	0.8	4.1	3.9	3.7	1.7	5.9	6.6	0.9

TABLE III  
PHASES CONTENT (%) FROM X-RAY (HT 1: 838 °C).

	Tape 1		Tape 2		Tape 3		Tape 4		Tape 5		Tape 6		Tape 7	
	HT 1	HT 2	HT 1	HT 2	HT 1	HT 2	HT 1	HT 2	HT 1	HT 2	HT 1	HT 2	HT 1	HT 2
Bi-2223	85.3	94.3	82	81.1	83.6	84.7	69.4	82.9	83.9	91.6	86.2	84.0	87.7	96.2
Bi-2212	10.1	3.8	9.8	17.8	7.8	12.7	16.0	12	10.7	5.6	6.9	10.9	5.3	2.9
Bi-2201	0.9	~0	1.6	~0	2.6	~0	9.7	0.9	1.8	~0	1.7	0.8	1.8	~0
Bi-3221	3.7	1.9	6.6	2.4	6.0	2.5	4.9	4.3	3.6	2.8	5.2	3.4	5.3	1

TABLE IV  
PHASES CONTENT (%) FROM X-RAY (HT 1: 842 °C).

	Tape 1		Tape 2		Tape 3		Tape 4		Tape 5		Tape 6		Tape 7	
	HT 1	HT 2	HT 1	HT 2	HT 1	HT 2	HT 1	HT 2	HT 1	HT 2	HT 1	HT 2	HT 1	HT 2
Bi-2223	86.4	95.7	83.3	84.3	88.5	95.2	20.9	86.4	82.0	93.5	89.3	88.5	87.0	94.8
Bi-2212	8.2	2.2	10.8	12.2	6.2	3.8	70.9	8.2	9.8	4.7	7.1	10.6	6.1	3.1
Bi-2201	0.9	~0	2.5	~0	1.8	~0	3.6	~0	2.5	~0	1.8	~0	1.7	~0
Bi-3221	4.5	2.2	3.3	3.5	3.5	1	4.5	5.5	5.7	1.9	1.8	0.9	5.2	2.1

strain was calculated by  $\% \varepsilon = t / \Phi_f \times 100$ , where  $t$  is the tape thickness and  $\Phi_f$  is the former diameter.

Hardness measurements were performed at room temperature using a Leco Microhardness Testing Machine (M-400-HI) and a 10 g load. Tapes (after heat treatment) were mounted in epoxy and polished to a 1  $\mu\text{m}$  finish, across the transverse direction of the tape. The hardness of the sheath was measured across a line between the outermost 2223 filament and the tape edge. An error of 3% in hardness readings was estimated.

The tensile strength of the tapes was measured at room temperature using a Lloyd instruments, LRX Plus tensile testing machine.

### III. RESULTS AND DISCUSSION

#### A. Optimum $I_c$ Dependence on Alloy Sheath Configurations

Fig. 1 shows the  $I_c$  of the tapes measured at 77 K and self-field after HT2. It is clearly seen that the  $I_c$  of all tapes is very low when HT1 = 846 °C compared with HT1 at other temperatures, and therefore 846 °C is well outside the optimum HT1 range. The highest  $I_c$  were achieved when HT1 = 838 °C for tapes 1 and 5, 840 °C for tapes 2, 3 and 4, 834 °C for tape 6 and 842 °C for tape 7. These results indicate that the tapes with different configurations of precursor and restack sheath materials need optimized HT1 conditions when all other processing conditions are the same.

#### B. Optimum $I_c$ Corresponds to Volume Fraction of Phases

Tables II–IV show the volume fractions of the Bi-2223, Bi-2212, Bi-2201 and Bi-3221 phases for the tapes after HT1 = 834 °C, 838 °C and 842 °C, and after HT2. Comparing

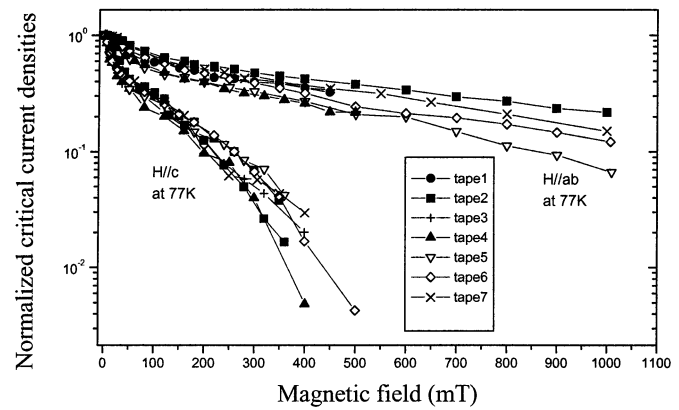


Fig. 2. Normalized  $J_c$  dependence on the magnetic field of the tapes at 77 K.

the  $I_c$  in Fig. 1 and the phase analyzes in Tables II–IV, it can be seen that the highest  $I_c$  is achieved when the volume fractions are 2223 > 90%, 2212 ~ 5%, 2201 ~ 0% and 3221 < 2%.

#### C. Normalized $J_c$ – Field Dependence and the Sheath Materials

Fig. 2 shows the relationship between the normalized  $J_c$  and the applied magnetic field, with the field perpendicular ( $H//c$ ) and parallel to the tape surface ( $H//ab$ ) at 77 K for the different tapes 1, 3, 5, 6 & 7 with HT1 = 838 °C, and tapes 2 & 4 with HT1 = 842 °C. The relationship between  $J_c$  and magnetic field is characteristic of multifilamentary 2223 tapes fabricated using a PIT technique. No conclusive correlation between alloy type or configuration and  $I_c$  performance in field was highlighted.

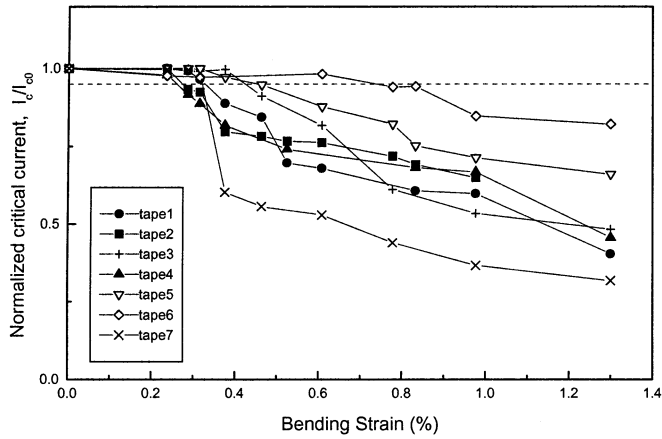


Fig. 3. Relative  $I_c/I_{c0}$  as a function of bend strain.

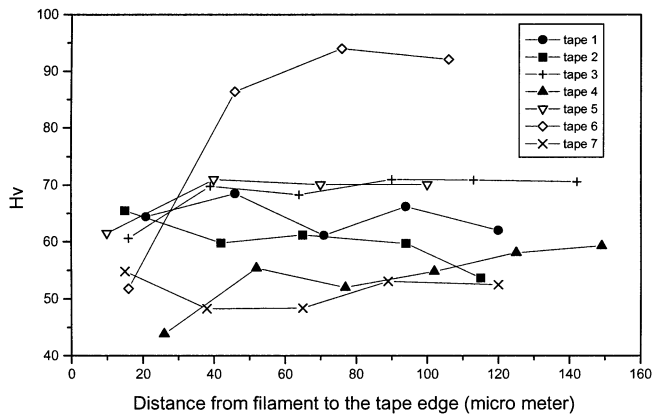


Fig. 4. The hardness profiles in the sheath materials of the tapes.

#### D. Bend Strain and the Sheath Materials

The results of the one-way bend test for the tapes 1 – 7 with  $HT1 = 840^\circ\text{C}$  are shown in Fig. 3. It was clearly observed that the tolerance of  $I_c$  to bending was quite different for the various tapes. The critical bend strain,  $\varepsilon_{\text{crit}}$  (bend strain when  $I_c/I_{c0} = 0.95$ ) of tapes 1 and 7 was approximately 0.3%; while the  $\varepsilon_{\text{crit}}$  of tapes 3 and 5 was 0.42% and 0.47%. Tapes 2 and 4 had  $\varepsilon_{\text{crit}}$  of 0.28% and 0.25%. Tape 6 possessed the highest  $\varepsilon_{\text{crit}}$  of 0.73%, displaying best performance of  $I_c$  tolerance to bend strain. From these results it was concluded that tapes with like restack sheath materials had similar bend strain properties and that the improved tolerance to bend strain could be related to the mechanical properties of the sheath materials.

#### E. Hardness Profiles and the Sheath Materials

The hardness of the sheath materials (tapes with  $HT1 = 840^\circ\text{C}$ ) are shown in Fig. 4. A line in Fig. 5 shows the region in the tape cross-section on which the microhardness distribution was examined. From Fig. 4, tape 6 with Mg in the restack sheath shows the highest hardness of  $\sim 90$  Hv. The sheaths of tapes 3 and 5 containing Sb, show the next level of hardness at approximately 70 Hv. The lowest level of hardness (50  $\sim$  60 Hv) was measured in those tapes with Au or pure Ag in the restack sheath. The sequence of the sheath hardness from highest to lowest was therefore AgMg0.2 wt%, AgSb0.6 wt%, AgAu7 wt% or Ag. These results are consistent

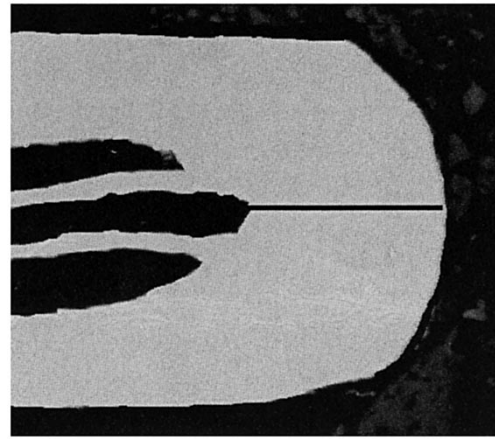


Fig. 5. A line shows the region in the tape cross-section on which the microhardness distribution was examined.

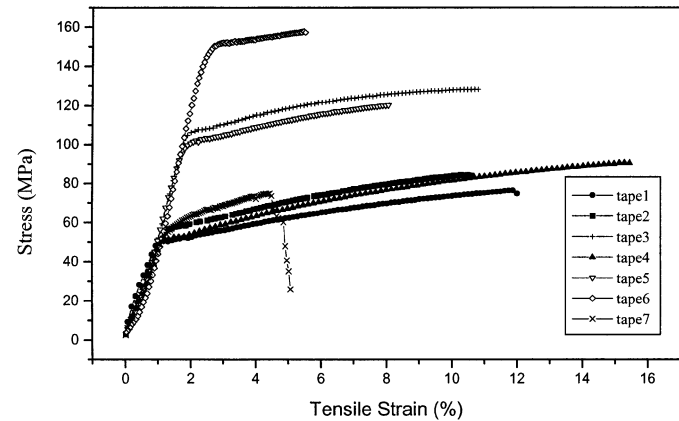


Fig. 6. The stress-strain relationship of the tapes measured at room temperature.

with the bend strain performance revealed in the previous section. Harder restack sheaths, such as those with Mg or Sb, must provide a mechanism by which the tolerance of the Bi-2223 to bend strain can be improved.

#### F. Tensile Strength and the Sheath Materials

The tensile strength of the tapes (with  $HT1 = 840^\circ\text{C}$ ) are shown in Fig. 6. The best strengthening effect was showed by tape 6 in which the restack sheath contained Mg. Tape 3 and tape 5 in which the restack sheath contained Sb, had the next best strengthening effect. Tapes 2, 4 and 7 were similar to tape 1 (pure Ag sheath) indicating that the use of Au has negligible effect on tensile strength. This trend was also consistent with the assessment of the bend strain tolerance.

## IV. CONCLUSIONS

Ag, AgAu7 wt%, AgSb0.6 wt% and AgMg0.2 wt% alloys were used as precursor and restack sheath materials for fabricating 37 filament Bi-2223 tapes using a PIT technique with a two-stage heat treatment process.

Analysis of the  $I_c$  and volume fractions of the Bi-2223, Bi-2212, Bi-2201 and Bi-3221 phases indicated that volume fractions of Bi-2223  $> 90\%$ , Bi-2212  $\sim 5\%$ , Bi-2201  $\sim 0\%$  and Bi-3221  $< 2\%$  normally result in tapes with the highest  $I_c$

The normalized  $J_c$  dependence on magnetic field of the tapes at 77 K and  $H//ab$  were compared. The relationship between  $J_c$  and magnetic field was characteristic of multifilamentary 2223 tapes fabricated using a PIT technique. No conclusive correlation between alloy type or configuration and  $I_c$  performance in field was highlighted.

The sequence of the critical bend strains,  $\varepsilon_{\text{crit}}$  of the tapes is 0.73% for tape 6, 0.42% & 0.47% for tapes 3 and 5,  $\sim 0.3\%$  for tapes 1 and 7, and 0.28% & 0.25% for tapes 2 and 4. Tapes with like restack sheath materials had similar bend strain properties. The variation in the bend strain tolerance of the tapes was consistent with the results of the hardness and tensile strength measurements. It was observed that the sequence of the sheath hardness and tensile strength from highest to lowest was AgMg0.2 wt%, AgSb0.6 wt%, AgAu7 wt% or Ag corresponding to the ranking of bend strain tolerance.

#### ACKNOWLEDGMENT

The authors would like to thank J. Volf for sample preparation.

#### REFERENCES

[1] H. Fujishiro, M. Ikebe, K. Noto, M. Matsukawa, T. Sasaoka, J. Sato, and S. Kuma, "Low thermal conductivity Bi-2223 tapes sheathed with Ag-Au alloys," *IEEE Transactions on Magnetics*, pt. 2, vol. 30, no. 4, pp. 1645–1650, 1994.

[2] L. Martini, F. Barberis, R. Berti, L. Bigoni, F. Curcio, and G. Volpini, "Optimization of multilayered Bi-2223/Ag-Au conductors for current lead applications," *International Journal of Modern Physics B*, vol. 13, no. 9–10, pp. 1357–1362, 1999.

[3] T. Sasaoka, K. Nomura, J. Sato, S. Kuma, H. Fujishiro, M. Ikebe, and K. Noto, "Characteristics of Ag-Au alloy sheathed Bi-Pb-Sr-Ca-Cu-O superconducting tapes for current leads," *Applied Physics Letters*, vol. 64, no. 10, pp. 1304–1305, 1994.

[4] W. Goldacker, E. Mossang, M. Quilitz, and M. Rikel, *IEEE Transactions on Applied Superconductivity*, vol. 7, no. 2, pp. 1407–1410, 1997.

[5] J. Yoo, H. Chung, J. Ko, and H. Kim, "Long-length processing of BSCCO-2223 tapes made by using Ag alloys sheath," *IEEE Transactions on Applied Superconductivity*, vol. 7, no. 2, pp. 1837–1840, 1997.

[6] K. Fischer, T. Fahr, A. Hütten, U. Schläfer, M. Schubert, C. Rodig, and H.-P. Trinks, "Technology of Bi,Pb-2223 tape fabrication with Ag and Ag alloy sheaths for electric power systems," *Supercond. Sci. Technol.*, vol. 11, pp. 995–1000, 1998.

[7] M. Apperley, R. Zeng, F. Darmann, and G. McCaughey, "Properties of Ag-Mg alloy sheathed Bi-2223 tapes," *Cryogenics*, vol. 40, pp. 319–324, 2000.

[8] M. Ishizuka, Y. Tanaka, T. Hashimoto, and H. Maeda, "Influences of Cu composition and sintering condition in Bi-2223 tapes using Ag-Cu alloy sheath doped with Ti, Zr or Hf," *Physica C*, vol. 290, no. 3–4, pp. 265–274, 1997.

[9] Y. Tanaka, F. Matsumoto, H. Maeda, and M. Ishizuka, "Improved  $J_c$  property of Bi2223 tapes made using AgCu alloy sheath doped with Ti, Zr, Hf or Au," *IEEE Transactions on Applied Superconductivity*, vol. 5, no. 2, pp. 1158–1161, 1995.

[10] R. P. Aloysius, A. Sobha, P. Guruswamy, and U. Syamaprasad, "Bend strain and tensile stress characteristics of (Bi,Pb)-2223/Ag-Cu alloy sheathed tapes," *Supercond. Sci. Technol.*, vol. 14, pp. 85–89, 2001.

[11] M. Putti, M. R. Cimberle, C. Ferdeghini, G. Grasso, A. Manca, and W. Goldacker, "Study of Bi(2223) tapes with low thermal conductivity," *IEEE Transactions on Applied Superconductivity*, vol. 11, no. 1, pp. 3285–3288, 2001.

[12] R. Zeng, Y. C. Guo, Y. Tanaka, J. Horvat, M. Ionescu, T. P. Beales, M. Apperley, H. K. Liu, and S. X. Dou, "Effect of the phase formation of Bi-2223 in some Ag-alloy sheathed PIT tapes," *Physica C*, vol. 307, pp. 229–236, 1998.