

Faculty of Engineering
Faculty of Engineering - Papers

University of Wollongong

Year 2006

The doping effect of multiwall carbon
nanotube on MgB₂/Fe superconductor
wire

J. H. Kim* W. K. Yeoh[†] M. J. Qin[‡]
X. Xu** S. X. Dou^{††}

*University of Wollongong, jhk@uow.edu.au

[†]University of Wollongong

[‡]University of Wollongong, qin@uow.edu.au

**University of Wollongong

^{††}University of Wollongong, shi@uow.edu.au

This article was originally published as Kim, JH, Yeoh, WK, Qin, MJ, Xu, X & Dou, SX, The doping effect of multiwall carbon nanotube on MgB₂/Fe superconductor wire, Journal of Applied Physics, July 2006, 100, 013908. Copyright American Institute of Physics. Original journal available <[a href="http://jap.aip.org/jap/"](http://jap.aip.org/jap/)>here.

This paper is posted at Research Online.

<http://ro.uow.edu.au/engpapers/153>

The doping effect of multiwall carbon nanotube on MgB₂/Fe superconductor wire

J. H. Kim,^{a)} W. K. Yeoh, M. J. Qin, X. Xu, and S. X. Dou

Institute for Superconducting and Electronic Materials, University of Wollongong, Northfields Avenue, Wollongong, New South Wales (NSW) 2522, Australia

(Received 14 December 2005; accepted 20 April 2006; published online 10 July 2006)

We evaluated the doping effect of two types of multiwall carbon nanotubes (CNTs) with different aspect ratios on MgB₂/Fe monofilament wires. Relationships between microstructure, magnetic critical current density (J_c), critical temperature (T_c), upper critical field (H_{c2}), and irreversibility field (H_{irr}) for pure and CNT doped wires were systematically studied for sintering temperature from 650 to 1000 °C. As the sintering temperature increased, T_c for short CNT doped sample slightly decreased, while T_c for long CNT doped sample increased. This indicates better reactivity between MgB₂ and short CNT due to its small aspect ratio, and substitution of carbon (C) from short CNT for boron (B) occurs. In addition, short CNT doped samples sintered at high temperatures of 900 and 1000 °C exhibited excellent J_c , and this value was approximately 10^4 A/cm² in fields up to 8 T at 5 K. This suggests that short CNT is a promising carbon source for MgB₂ superconductor with excellent J_c . In particular, inclusion of nanosized MgO particles and substitution of C into the MgB₂ lattice could result in strong flux pinning centers. © 2006 American Institute of Physics. [DOI: 10.1063/1.2209188]

INTRODUCTION

MgB₂ is one of the most promising materials for superconductor applications.¹ The high transition temperature of 39 K gives us many advantages for industrial applications where cooling costs and system stability are of concern. The low material cost of magnesium (Mg) and boron (B) is an additional advantage. Furthermore, thanks to its large coherence length and two-gap superconductivity, the opportunity exists to enhance critical current density (J_c) and upper critical field (H_{c2}) by doping with a wide variety of additives or with substitutional dopants.^{2,3} A number of carbon sources, such as SiC, C, B₄C, and carbon nanotube (CNT), have shown positive effect on J_c and H_{c2} , but have resulted in a large drop in critical temperature (T_c).⁴⁻⁹ Among the various carbon sources, CNTs are particularly interesting as their special geometry may induce effective superconductivity.

It is widely known that CNTs have good electrical, thermal, and mechanical properties, although they exhibit some particularities because of their high aspect ratio and nanometer scale diameters.¹⁰ Many properties of CNT are directly influenced by the way the graphene sheets are wrapped around. The most important CNT structures are those of single walled nanotubes (SWNTs) and multiwalled nanotubes (MWNTs). A SWNT is considered as a cylinder with only one wrapped graphite sheet. MWNT are similar to a collection of concentric SWNTs. The length and diameter of these structures differ a lot from those of SWNTs and their properties are also very different. Specifically, MWNTs can carry current densities up to 10^9 – 10^{10} A/cm² and have good thermal conductivity of 3000 W/mK.^{11,12} These properties could benefit heat dissipation and thermal stability for MgB₂ wires. In addition, MWNT can be used for both the carbon

source and as mechanical supports because of its high axial strength.¹³ Therefore, including MWNT in MgB₂ wire is attractive for superconducting applications.

In the literature, Wei *et al.* have studied the superconductivity of MgB₂-CNT composites.¹⁴ Dou *et al.* studied the doping effects of CNT on the T_c , J_c , and lattice parameters of MgB_{2-x}C_x with $x=0, 0.05, 0.1, 0.2,$ and 0.3 .⁷ The substitution of C from CNT was found to enhance J_c in magnetic field but depressed T_c . Recently, Yeoh *et al.* reported that the effect of CNT doping on H_{c2} and irreversibility field (H_{irr}).¹⁵ However, the effects of CNT shape (aspect ratio: length over diameter) on the superconductivity of MgB₂ were not systematically evaluated. In addition, these researchers estimated the fundamental properties from pellet samples. In this study, we fabricated MgB₂/Fe monofilament wires doped with different length CNTs and evaluated the T_c , magnetic J_c , microstructures, H_{c2} , and H_{irr} . The resulting properties were compared with a pure MgB₂/Fe sample.

EXPERIMENTAL PROCEDURE

MgB₂/Fe monofilament wires were prepared by an *in situ* reaction process and powder-in-tube method. Powders of Mg (99%), amorphous B (99%), and CNT (>95%) were used as starting materials. We prepared two kinds of multiwalled CNTs as carbon sources for comparison. One had a length (L) of 0.5–200 μm and outer diameter (o.d.) of <8 nm, and the other had with L of 0.5 μm and o.d. of 20–30 nm (hereafter called long and short CNTs, respectively, referring to the length of the CNT). These powders were well mixed with Mg and B powders, having the composition of MgB_{1.8}C_{0.2}. The mixed powders were packed into iron (Fe) tubes with a L of 140 mm. The Fe tube had an o.d. of 10 mm and an inner diameter (i.d.) of 8 mm. The packing process was carried out in air. Both ends of the tubes were

^{a)}Electronic mail: jhk@uow.edu.au

sealed with aluminium pieces. The composites were drawn to o.d. of 1.42 mm. These fabricated wires were sintered at 650–1000 °C for 30 min under high purity argon (Ar) gas. The heating rate was 5 °C/min. After sintering, the wires were furnace cooled to room temperature. A pure MgB₂/Fe wire was also fabricated for comparison by applying the same processing. The volume fraction of the superconducting core in the final wire was approximately 48%.

The microstructure of the wires was evaluated by scanning electron microscope (SEM), transmission electron microscope (TEM), and x-ray diffraction (XRD). Magnetization and ac susceptibility were measured by a physical property measurement system (PPMS) (Quantum Design). The magnetic critical current density (J_c) was derived from the height of the magnetization loop using Bean's model. Magnetic fields up to 8.0 T were applied parallel to the wire axis of the MgB₂ core at 5 and 20 K. To calculate the magnetic J_c of a MgB₂/Fe wire, we first removed the Fe sheath by a mechanical process because this material has ferromagnetic properties. All samples were made to the same size of an o.d. of 0.98 mm and L of 2.5 mm, in order to reduce the sample size effect.¹⁶ Critical temperature (T_c) was defined as the onset temperature at which diamagnetic properties were observed. The resistance (R) versus temperature (T) curves were evaluated in magnetic field up to 8.7 T by the standard four-probe method using PPMS. From these curves, we defined the H_{c2} and H_{irr} as $H_{c2}=0.9R(T_c)$ and $H_{irr}=0.1R(T_c)$, respectively.

RESULTS AND DISCUSSION

Figure 1 shows the XRD patterns of short and long CNT doped MgB₂/Fe wires with nominal composition of MgB_{1.8}C_{0.2} after sintering at various temperatures for 30 min. XRD measurements were performed on the ground MgB₂ core samples. This figure also shows the XRD patterns of both short and long CNT powders for comparison. As can be seen in this figure, the diffraction patterns of both CNTs showed a broad peak, indicating an amorphouslike phase. Due to their intrinsic nature, the features of XRD patterns of CNTs were close to those of graphite.¹⁷ These phases were not clearly observed in the XRD patterns of CNT doped MgB₂/Fe after sintering. However, small amount of unreacted CNT could exist in the MgB₂ core, because the CNT peak overlaps the MgB₂ (101) peak at $2\theta \approx 42.5$. In addition, a backgroundlike feature indicates amorphous phase at low 2θ for CNT doped MgB₂ wire, suggesting that unreacted CNT may remain within the MgB₂ core. It has been reported that full substitution of C for B site could not be completed, even at a sintering temperature of 1000 °C.¹⁸ We observed that all samples sintered at different temperatures from 650 to 900 °C seem to be well developed MgB₂ with small amounts of MgO. It can be observed that the XRD patterns of the CNT doped MgB₂/Fe wire are almost independent of the sintering temperature. For the 1000 °C sintering temperature, however, we observed diffraction peaks of Mg and Fe_xB (Fe₂B, FeB) for MgB₂/Fe wire.^{19,20} Fe₂B(FeB) may be formed due to chemical reactions between the Fe tube and the MgB₂, which results in a small amount of remnant Mg

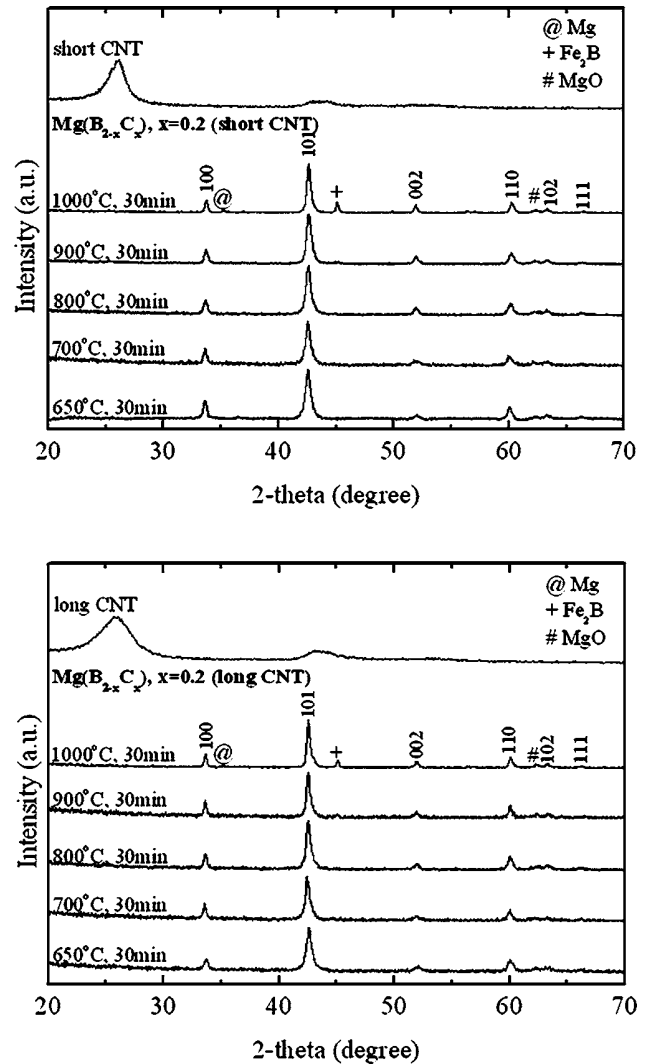


FIG. 1. The x-ray diffraction patterns for short and long CNT doped MgB₂ wires with nominal composition of MgB_{1.8}C_{0.2} after sintering at various temperatures for 30 min. The patterns of the precursor CNT powders are also shown for comparison.

phase. Another possibility is that the loss of Mg due to the high sintering temperature results in excess B, which reacts with Fe tube to form Fe₂B(FeB). From SEM observation, we could see a thin layer in the contact area between the Fe tube and the Mg. Thus, it is difficult to maintain the stoichiometry of MgB₂ at high sintering temperature.

From the XRD patterns, we also evaluated the full width at half maximum (FWHM) of the (100) peak ($2\theta \approx 33.5^\circ$) for pure and CNT doped MgB₂/Fe wires. The FWHM is related to the crystallinity and lattice distortion. The FWHM of pure wire decreased as the sintering temperature increased. The FWHM values for pure wire were calculated to be 0.366°, 0.320°, 0.326°, 0.308°, and 0.250° at sintering temperatures of 650, 700, 800, 900, and 1000 °C, respectively. This result can be explained by the improved crystallinity of the MgB₂ core, indicating that the grain size increases with sintering temperature.²¹ The FWHM behavior of long CNT doped wire as a function of sintering temperature was similar to that of pure wire. However, FWHMs of

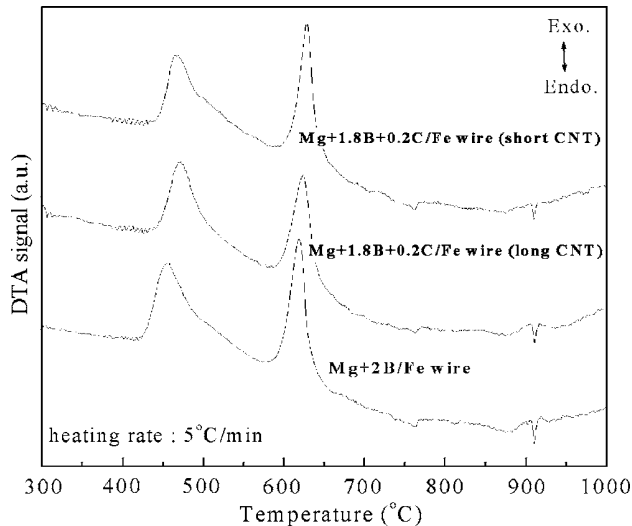


FIG. 2. The DTA curves for pure and CNT doped wires processed with a heating rate of 5 °C/min.

short CNT doped wire increased with annealing temperature. The FWHMs were 0.350°, 0.392°, and 0.400° at annealing temperatures of 650, 700, and 900 °C, respectively. Thus indicates that lattice distortions occur due to short CNT doping.

Figure 2 shows differential thermal analysis (DTA) traces of pure and CNT doped MgB_2/Fe wires fabricated by an *in situ* process. In order to maintain the same sintering conditions, heating rates were 5 °C/min under high purity Ar gas. For pure MgB_2/Fe wire, i.e., $\text{Mg}+2\text{B}/\text{Fe}$, the first exothermic peak was observed at around 457 °C, which corresponds to the formation of MgO and melting of B_2O_3 .²² The melting temperature of B_2O_3 is approximately 450 °C. The MgO formation is considered to be due to the reaction between melting B_2O_3 and Mg, i.e., Mg reacts with B_2O_3 to form $\text{MgO}+\text{B}$. The B_2O_3 as the second phase is related to purity of starting powders. The other reason of the existence of MgO in the final wires is because the surface of the commercial Mg powder has partially oxidized. Thus, starting powders with high purity are important for the superconducting properties. The second exothermic peak at 619 °C was due to the reaction between melting Mg and amorphous B to form MgB_2 . These results are consistent with those of Guldacker *et al.*²² For CNT doped wires, however, the first exothermic peaks were slightly shifted to the higher temperature direction. This is related to the additional impurity due to CNT doping in the starting powders. It is to be noted that the reaction temperature of $\text{MgB}_{1.8}\text{C}_{0.2}$ formation is almost independent of the aspect ratio between long and short CNTs.

A narrow endothermic peak around 910 °C is related to a structural transition of Fe sheath material. According to the Fe– Fe_3C phase diagram, α -Fe (ferrite) with bcc structure transforms into γ -Fe (austenite) with fcc structure at around 912 °C.²³ In general, the tetrahedral interstitial site for ferrite is relatively bigger than the octahedral site. Atoms with a maximum radius of 0.35 Å can fit. On the other hand, the octahedral site for austenite is relatively bigger than the tetrahedral site. Atoms with a maximum radius of 0.51 Å can

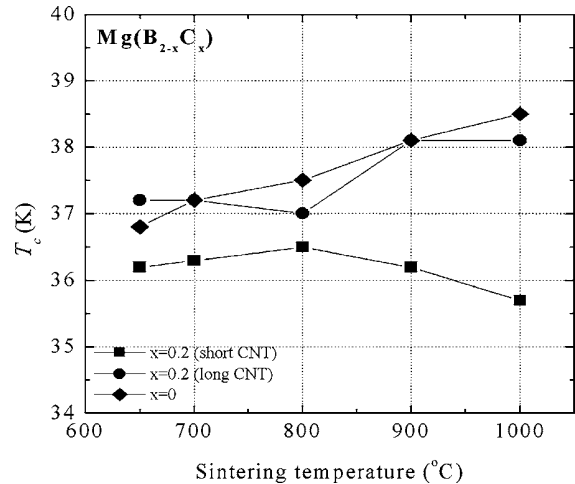


FIG. 3. The relationships between T_c and sintering temperature for pure and CNT doped wires.

now fit. For this reason, it is easy for Fe and B to react above the sintering temperature of 912 °C. Iron boride (Fe_2B , $2\theta \approx 45.1^\circ$), especially, can be easily formed at a Fe/Mg ratio greater than 0.02.

The critical temperatures (T_c) for pure, short, and long CNT doped MgB_2/Fe wires are presented in Fig. 3. For pure MgB_2/Fe wire, T_c increased systematically as the sintering temperature increased. This is related to the improvement of crystallinity of the MgB_2 core. It is to be noted that the T_c variations of the doped wires are significantly different for the two types of CNTs. As the sintering temperature increased, T_c for the short CNT sample slightly decreased, on the other hand, T_c for the long CNT sample increased. In addition, T_c of short CNT doped wire was slightly lower than for the long one at the same sintering temperature. For example, T_c values of long CNT doped wire were 37.2, 37.0, and 38.1 K at 650, 800, and 1000 °C, respectively, while the corresponding values for the short one were 36.2, 36.5, and 35.7 K. This result is considered to be due to better reactivity between MgB_2 and short CNT. Since the short CNT has a smaller aspect ratio. On the other hand, long CNT has a higher aspect ratio and tends to entangle, preventing homogeneous mixing in MgB_2 . In order to explore other possibilities, we also estimated the core density of pure and CNT doped wires. The core density improved in all samples with sintering temperature. The mean values were calculated to be 1.33, 1.42, and 1.42 g/cm³ in pure, short, and long CNT doped wires, respectively. Even though the density of our pure sample (1.33 g/cm³) was not closed to the theoretical density (2.62 g/cm³), the density values of both CNT doped wires were the same. We found that the actual doping reactivity between CNT and MgB_2 is strongly influenced by the shape of carbon source.

Figure 4 shows the magnetic dependence of J_c for short and long CNT doped wires at 5 and 20 K. The best $J_c(B)$ result of pure MgB_2 wire is also plotted for comparison and was estimated to be 0.34 MA/cm² at 20 K in self-field. It was observed that J_c for the short CNT doped sample was much higher than that for the long one. Specifically, the short CNT doped samples sintered at high temperatures of 900 and

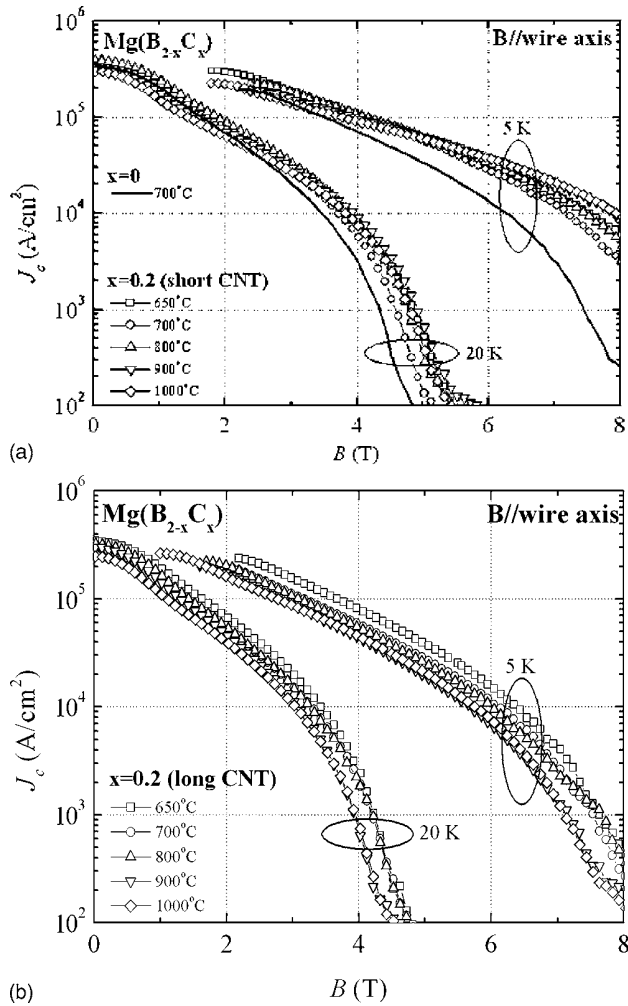


FIG. 4. Critical current densities for (a) short CNT doped and (b) long CNT doped wires sintered at various temperatures for 30 min. Magnetic J_c curves of pure MgB_2 wires sintered at 700°C for 30 min are also shown for comparison.

1000°C exhibited excellent J_c , approximately 10^4 A/cm² in fields up to 8 T at 5 K. In addition, J_c of the sample sintered at the highest temperature showed a crossover with that of the low temperature one around 5 T. This result indicates that flux pinning after high temperature sintering was enhanced by a large amount of C substitution. It is to be noted that J_c for the long CNT doped sample was depressed monotonically as the sintering temperature increased. This behavior is likely to be related to the increasing of MgB_2 grain size due to inhomogeneous mixing. As mentioned above, FWHM of the long CNT doped wire decreased with annealing temperature, indicating that grain size increases. Many groups have reported that the increase of grain size in MgB_2 is an important factor in the suppression of J_c , since grain boundary pinning is an important mechanism in controlling J_c .^{4,24–26} In addition, we observed that there was no crossover around 5 T. This behavior is similar to that of the pure MgB_2 wire, and J_c was $<10^3$ A/cm² at 8 T and 5 K. Poor field performance for long CNT doped wire is likely to be ultimately related to the poor reactivity and inhomogeneous mixing between MgB_2 and long CNT.

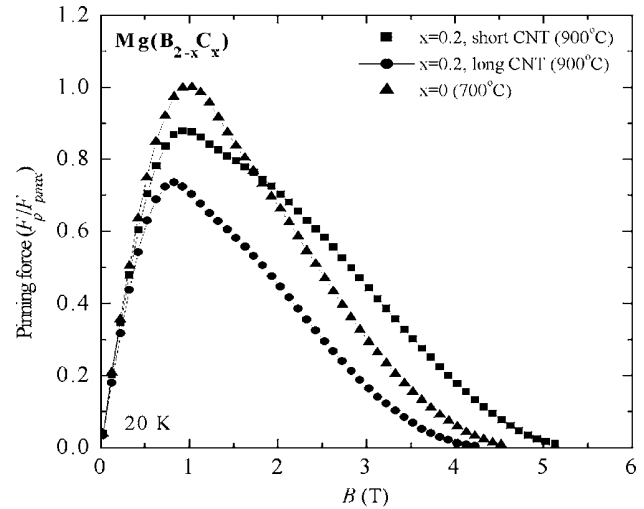


FIG. 5. The field dependence of the volume pinning force, $F_p = J \times B$, of short and long CNT doped MgB_2 wires at 20 K. The F_p is normalized by the maximum volume pinning force $F_{p,\text{max}}$ of pure MgB_2 .

In order to evaluate the reactivity, we measured the specific surface area (SSA) of both CNTs and B powder using surface area analyser (NOVA 1000) and the well-known Brunauer-Emmett-Teller (BET) equation. It was observed that the SSA of long CNT was much bigger than that of the short one. The measured SSAs were 31.50, 120.43, and 408.50 m²/g for B powder, short CNT, and long CNT, respectively. From this result, one would expect long CNT to be more reactivity. However, magnetic J_c of this sample was the same as for the pure one. This is because the surface of CNT is very stable. Even though long CNT has a bigger surface area, compared to short CNT, only the end holes of CNT are effective as reaction site.^{27,28} Generally, the properties of the CNTs are influenced by defect sites on the walls and at the ends. The caps at both ends of the CNTs are removed, and defects on surface are revealed by purification techniques.

Figure 5 plots the field dependence of the volume pinning force, $F_p = J \times B$, of short and long CNT doped samples at 20 K. The F_p is normalized by the maximum volume pinning force $F_{p,\text{max}}$ of pure MgB_2 . When $0 < B < 0.5$ T, the shapes of these plots were almost the same as that of the pure sample. For the wires at $0.5 < B < 2.0$ T, it was observed that the pure MgB_2 sample is much more conducive to obtaining a strong $F_p(B)$. At $B > 2.0$ T, however, the $F_p(B)$ of the short CNT doped sample is larger than that of the pure and long CNT doped samples. This result indicates that the $F_p(B)$ of the MgB_2 tapes was improved by the doping effect of short CNT. It is to be noted that $F_p(B)$ behavior of the long CNT doped sample was similar to that of the short CNT doped sample. A similar flux pinning mechanism is likely to be involved for both CNT doped samples.

Figure 6 shows TEM images for short [(a) and (b)] and long [(c) and (d)] CNT doped MgB_2 sintered at 900°C . In all the specimens, the powders were suspended on “lacey carbon grids,” that is, a network of carbon filaments. As can be seen from the figures, the short CNT doped samples consisted of crystalline MgB_2 grains of 100–200 nm, small

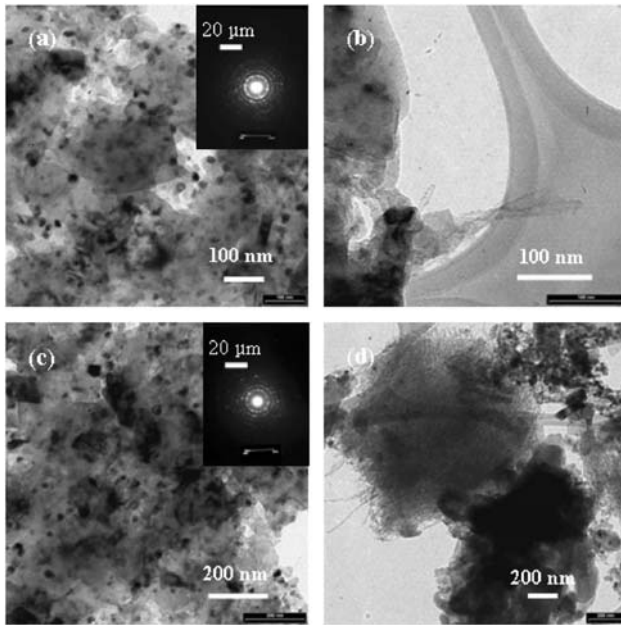


FIG. 6. TEM images for short CNT doped [(a) and (b)] and long CNT doped [(c) and (d)] MgB_2 wires with the nominal composition of $\text{MgB}_{1.8}\text{C}_{0.2}$. The insets in (a) and (c) show ring-type diffraction patterns consistent with MgB_2 +another phase, possibly MgO .

MgB_2 grains of 10–20 nm in size, and nanoparticles. From energy dispersive x-ray (EDX) spectra, these particles were rich in oxygen. However, it is difficult to know the exact composition of the nanoparticles. These nanoparticles could be related to the CNT doping. Some areas [such as (b)] showed CNT sticking out of MgB_2 grain and little lumps of CNT. For the long CNT doped sample, on the other hand, we observed large lumps of unreacted CNT near MgB_2 grains [see (d)]. Because of the entanglement of long CNT due to the high aspect ratio, long CNT is difficult to align along the direction of the wire axis during mechanical processing. However, there also appears to be a large number of very small grains and nanoparticles. Diffraction patterns, shown in the top right corners [(a) and (c)], gave ring type patterns consistent with MgB_2 . There are extra rings in these patterns, which suggest another phase, i.e., these rings appear to be consistent with MgO . According to two-gap superconductivity, the nanoparticles could enhance the flux pinning effect. Since the a - b plane coherence length of MgB_2 is approximately 6–7 nm, partial inclusion of nanosized particles could result in strong flux pinning centers.²⁹

It is to be noted that there are no nanoparticles within the pure MgB_2 matrix. However, the magnetic J_c of pure MgB_2 sintered at 700 °C was the same as that of the long CNT doped one sintered at 900 °C, as mentioned above. This is because a small MgB_2 grain size allows the extra grain boundaries to also act as strong flux pinning centers. The pure samples sintered at 700 °C consisted of MgB_2 grains of 50–150 nm. Yamada *et al.* reported that the small MgB_2 grain size was effective in enhancing flux pinning because the grain boundaries of MgB_2 represented effective pinning centers, as in the case of A15 metallic superconductors.²⁵ Fischer *et al.* fabricated MgB_2 wires and bulks by a mechani-

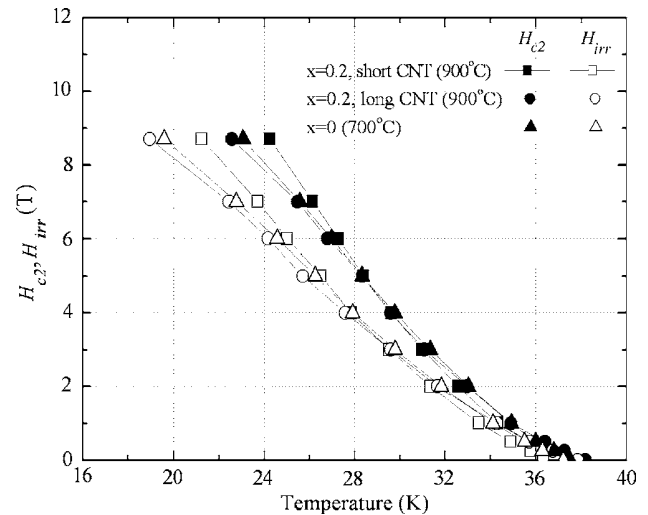


FIG. 7. Temperature dependence of H_{c2} and H_{irr} for short and long CNT doped MgB_2 sintered at 900 °C. The H_{c2} and H_{irr} of pure MgB_2 wires sintered at 700 °C for 30 min are also shown for comparison.

cal alloying method.³⁰ They obtained one of the highest J_c values without any other element materials added. The very fine-grained nanocrystalline microstructure of the superconducting phase seems to be responsible for these excellent J_c values.³¹

The temperature dependence of H_{c2} and H_{irr} for short and long CNT doped MgB_2 sintered at 900 °C is shown in Fig. 7. As can be seen from the figure, the H_{c2} of the short CNT doped sample was higher than that of the long one, which was similar to that of the pure MgB_2 . The short CNT doped sample demonstrated larger dH_{c2}/dT , compared with the pure and the long one. These are believed to increase the intraband scattering, and shorten the mean free path and coherence length.⁶ In addition, H_{c2} - T curves of all samples show similar behavior to those of the H_{irr} - T curves. We also evaluated the resistivity of pure and CNT doped samples. The values were calculated to be 38.5, 57.5, and 2.60 $\mu\Omega$ cm at 40 K for the pure, short, and long CNT doped wires, respectively. The short CNT doped samples showed a relatively higher value of resistivity at 40 K. The increased resistivity for the short CNT doped sample could be due to the greater C substitution or to higher sample density. However, the long CNT doped sample had a lower resistivity, compared to the pure sample. From the resistivity curve, the residual resistivity ratio (RRR) was estimated to be 2.02, 1.98, and 1.63 for the pure, long, and short CNT doped samples, respectively.³²

CONCLUSION

In this study, we evaluated the doping effect of CNT with different aspect ratios on MgB_2/Fe monofilament wires. Relationships between microstructure, J_c , T_c , H_{c2} , and H_{irr} for both short and long CNT doped wires were systematically studied. We observed that all samples sintered at different temperatures from 650 to 900 °C seem to be a well-developed MgB_2 with small amount of MgO . However, the FWHM of the (100) peak of the short CNT doped wire increased with sintering temperature. This indicates that lattice

distortion and depressed crystallinity have occurred due to short CNT doping. Specifically, short CNT doped samples sintered at high temperatures exhibited excellent J_c , $\sim 10^4$ A/cm² up to 8 T at 5 K. The J_c of the sample sintered at the highest temperature showed a crossover with that of the low temperature one around 5 T. This result indicates that flux pinning for samples produced at a high sintering temperature was enhanced by short CNT doping. In addition, the short CNT doped sample presented a larger dH_{c2}/dT , compared with the pure and the long one. The short CNTs are thus believed to increase the intraband scattering and shorten the mean free path and coherence length. The short CNT is a promising carbon source for MgB₂ superconductor with excellent J_c .

ACKNOWLEDGMENTS

The authors thank Dr. T. Silver, Dr. J. Horvat, Dr. R. H. T. Wilke, and R. Kinnell for their helpful discussions. This work was supported by the Australian Research Council, Hyper Tech Research, Inc., USA, Alphatech International Ltd., NZ, and the University of Wollongong.

- ¹J. Nagamatsu, N. Nakagawa, T. Muranaka, Y. Zenitani, and J. Akimitsu, *Nature (London)* **410**, 63 (2001).
- ²D. C. Larbalestier *et al.*, *Nature (London)* **410**, 186 (2001).
- ³A. Gurevich, *Phys. Rev. B* **67**, 184515 (2003).
- ⁴S. X. Dou, S. Soltanian, X. L. Wang, P. Munroe, S. H. Zhou, M. Ionescu, H. K. Liu, and M. Tomic, *Appl. Phys. Lett.* **81**, 3419 (2002).
- ⁵C. H. Cheng *et al.*, *Supercond. Sci. Technol.* **16**, 1182 (2003).
- ⁶A. Yamamoto, J. Shimoyama, S. Ueda, I. Iwayama, S. Horii, and K. Kishio, *Supercond. Sci. Technol.* **18**, 1323 (2005).
- ⁷S. X. Dou, W. K. Yeoh, J. Horvat, and M. Ionescu, *Appl. Phys. Lett.* **83**, 4996 (2003).
- ⁸R. A. Ribeiro, S. L. Bud'ko, C. Petrovic, and P. C. Canfield, *Physica C* **384**, 227 (2003).
- ⁹W. Mickelson, J. Cumings, W. Q. Han, and A. Zettl, *Phys. Rev. B* **65**,

- 052505 (2002).
- ¹⁰E. Thostenson, Z. Ren, and T. Chou, *Compos. Sci. Technol.* **61**, 1899 (2001).
- ¹¹B. Q. Wei, R. Vajtai, and P. M. Ajayan, *Appl. Phys. Lett.* **79**, 1172 (2001).
- ¹²P. Kim, L. Shi, A. Majumdar, and P. L. McEuen, *Phys. Rev. Lett.* **87**, 215502 (2001).
- ¹³M. M. J. Treacy, T. W. Ebbesen, and J. M. Gibson, *Nature (London)* **381**, 678 (1996).
- ¹⁴J. Wei, Y. Li, C. Xu, B. Wei, and D. Wu, *Mater. Chem. Phys.* **78**, 785 (2003).
- ¹⁵W. K. Yeoh, J. Horvat, S. X. Dou, and V. Keast, *Supercond. Sci. Technol.* **17**, S572 (2004).
- ¹⁶M. J. Qin, S. Keshavarzi, S. Soltanian, X. L. Wang, H. K. Liu, and S. X. Dou, *Phys. Rev. B* **69**, 012507 (2004).
- ¹⁷W. Zhu, D. Miser, W. Chan, and M. Hajaligol, *Mater. Chem. Phys.* **82**, 638 (2003).
- ¹⁸S. Lee, T. Masui, A. Yamamoto, H. Uchiyama, and S. Tajima, *Physica C* **397**, 7 (2003).
- ¹⁹R. Flükiger, H. L. Suo, N. Musolino, C. Beneduce, P. Toulemonde, and P. Lezza, *Physica C* **385**, 286 (2003).
- ²⁰M. Kühberger and G. Gritzner, *Physica C* **370**, 39 (2001).
- ²¹H. Kumakura, H. Kitaguchi, A. Matsumoto, and H. Yamada, *Supercond. Sci. Technol.* **18**, 1042 (2005).
- ²²W. Goldacker, S. I. Schlachter, B. Obst, and M. Eisterer, *Supercond. Sci. Technol.* **17**, S490 (2004).
- ²³R. E. Reed-Hill, *Physical Metallurgy Principles* (PWC, Boston, 1991).
- ²⁴S. X. Dou, V. Braccini, S. Soltanian, R. Klie, Y. Zhu, S. Li, X. L. Wang, and D. C. Larbalestier, *J. Appl. Phys.* **96**, 7549 (2004).
- ²⁵H. Yamada, M. Hirakawa, H. Kumakura, A. Matsumoto, and H. Kitaguchi, *Appl. Phys. Lett.* **84**, 1728 (2004).
- ²⁶H. Fang, S. Padmanabhan, Y. X. Zhou, and K. Salama, *Appl. Phys. Lett.* **82**, 4113 (2003).
- ²⁷H. Hu, P. Bhowmik, B. Zhao, M. A. Hamon, M. E. Itkis, and R. C. Haddon, *Chem. Phys. Lett.* **345**, 25 (2001).
- ²⁸D. B. Mawhinney, V. Naumenko, A. Kuznetsova, J. T. Yates, Jr, J. Liu, and R. E. Smalley, *Chem. Phys. Lett.* **324**, 213 (2000).
- ²⁹M. Xu *et al.*, *Appl. Phys. Lett.* **79**, 2779 (2001).
- ³⁰C. Fischer *et al.*, *Appl. Phys. Lett.* **83**, 1803 (2003).
- ³¹X. L. Liao, A. Serquis, Y. T. Zhu, J. Y. Huang, L. Civale, D. E. Peterson, F. M. Mueller, and H. F. Xu, *J. Appl. Phys.* **93**, 6208 (2003).
- ³²J. M. Rowell, *Supercond. Sci. Technol.* **16**, R17 (2003).