



UNIVERSITY  
OF WOLLONGONG  
AUSTRALIA

University of Wollongong  
Research Online

---

Faculty of Engineering - Papers (Archive)

Faculty of Engineering and Information Sciences

---

2012

# Fluctuation of mean free path and transition temperature induced vortex pinning in (Ba,K)Fe<sub>2</sub>As<sub>2</sub> superconductors

S R. Ghorbani

*University of Wollongong, ghorbani@uow.edu.au*

Xiaolin Wang

*University of Wollongong, xiaolin@uow.edu.au*

Mahboobeh Shahbazi

*University of Wollongong, msm979@uow.edu.au*

S. X. Dou

*University of Wollongong, shi@uow.edu.au*

C T. Lin

*Max-Planck-Institut fur Festkorperforschung, Heisenbergstrabe Stuttgart, Germany*

<http://ro.uow.edu.au/engpapers/4847>

---

## Publication Details

Ghorbani, S. R., Wang, X. L., Shahbazi, M., Dou, S. X. & Lin, C. T. (2012). Fluctuation of mean free path and transition temperature induced vortex pinning in (Ba,K)Fe<sub>2</sub>As<sub>2</sub> superconductors. *Applied Physics Letters*, 100 (21), 212601-1-212601-4.

Research Online is the open access institutional repository for the University of Wollongong. For further information contact the UOW Library:  
[research-pubs@uow.edu.au](mailto:research-pubs@uow.edu.au)

## Fluctuation of mean free path and transition temperature induced vortex pinning in (Ba,K)Fe<sub>2</sub>As<sub>2</sub> superconductors

S. R. Ghorbani, X. L. Wang, M. Shahbazi, S. X. Dou, and C.T. Lin

Citation: *Appl. Phys. Lett.* **100**, 212601 (2012); doi: 10.1063/1.4714543

View online: <http://dx.doi.org/10.1063/1.4714543>

View Table of Contents: <http://apl.aip.org/resource/1/APPLAB/v100/i21>

Published by the [American Institute of Physics](#).

---

### Related Articles

Para-conductivity and critical regime of (Tl<sub>1-x</sub>Cx)Ba<sub>2</sub>Ca<sub>3</sub>Cu<sub>4</sub>O<sub>12-δ</sub> superconductors

*J. Appl. Phys.* **112**, 033912 (2012)

The electrical conductivity of bundles of superconducting nanowires produced by laser ablation of metals in superfluid helium

*Appl. Phys. Lett.* **101**, 052605 (2012)

Spin-dependent transport properties through gapless graphene-based ferromagnet and gapped graphene-based superconductor junction

*J. Appl. Phys.* **112**, 013901 (2012)

Interstitial doping induced superconductivity at 15.3K in Nb<sub>5</sub>Ge<sub>3</sub> compound

*J. Appl. Phys.* **111**, 123912 (2012)

Microwave heating-induced static magnetic flux penetration in YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-δ</sub> superconducting thin films

*J. Appl. Phys.* **111**, 123911 (2012)

---

### Additional information on *Appl. Phys. Lett.*

Journal Homepage: <http://apl.aip.org/>

Journal Information: [http://apl.aip.org/about/about\\_the\\_journal](http://apl.aip.org/about/about_the_journal)

Top downloads: [http://apl.aip.org/features/most\\_downloaded](http://apl.aip.org/features/most_downloaded)

Information for Authors: <http://apl.aip.org/authors>

### ADVERTISEMENT



**HAVE YOU HEARD?**

Employers hiring scientists  
and engineers trust  
**physicstoday JOBS**



<http://careers.physicstoday.org/post.cfm>

## Fluctuation of mean free path and transition temperature induced vortex pinning in (Ba,K)Fe<sub>2</sub>As<sub>2</sub> superconductors

S. R. Ghorbani,<sup>1,2</sup> X. L. Wang,<sup>1,a)</sup> M. Shahbazi,<sup>1</sup> S. X. Dou,<sup>1</sup> and C.T. Lin<sup>3</sup>

<sup>1</sup>*Institute for Superconducting and Electronic Materials, University of Wollongong, Wollongong, New South Wales 2522, Australia*

<sup>2</sup>*Department of Physics, Hakim Sabzevari University, P.O. Box 397, Sabzevar, Iran*

<sup>3</sup>*Max-Planck-Institut für Festkörperforschung, Heisenbergstraße 1, D-70569 Stuttgart, Germany*

(Received 29 March 2012; accepted 25 April 2012; published online 21 May 2012)

The vortex pinning mechanisms of Ba<sub>0.72</sub>K<sub>0.28</sub>Fe<sub>2</sub>As<sub>2</sub> single crystal have been studied systematically as a function of temperature and magnetic field. The temperature dependence of the critical current density,  $J_c(T)$ , was analysed within the collective pinning model at different magnetic fields. It was found that both the  $\delta l$  pinning mechanism, i.e., pinning associated with charge-carrier mean free path fluctuation, and the  $\delta T_c$  pinning mechanism, which is associated with spatial fluctuations of the transition temperature, coexist in the Ba<sub>0.72</sub>K<sub>0.28</sub>Fe<sub>2</sub>As<sub>2</sub> single crystal in fields smaller than 4 T. Their contributions are strongly temperature and magnetic field dependent. At lower temperature and  $B \leq 4$  T, the  $\delta l$  pinning is the dominant mechanism, and its contributions decrease with increasing temperature. At temperatures close to the critical temperature, however, there is evidence for  $\delta T_c$  pinning. At magnetic fields larger than 4 T, the  $\delta l$  pinning mechanism is the only effect. © 2012 American Institute of Physics. [<http://dx.doi.org/10.1063/1.4714543>]

The main physical parameters of interest for using superconducting materials are: a high superconducting transition temperature,  $T_c$ , high critical current density,  $J_c$ , high upper critical field,  $B_{c2}$ , high irreversibility field,  $B_{irr}$ , strong magnetic-flux pinning, good grain connectivity, and a small anisotropy. The layered cuprate superconductors have high anisotropy, short coherence length, and high  $T_c$ . Therefore, the vortices mainly behave as two-dimensional (2D) pancake vortices at high temperatures and fields. Such vortices can move easily, and their fluctuations are quite strong.<sup>1</sup> Grain boundaries of high- $T_c$  superconductors have been a critical issue in practical applications. It is well known that the critical current exhibits exponential decay in the weak-link regime. In this regime, they have poor grain connectivity and easy melting of the vortex lattice, leading to small  $J_c$  in high magnetic fields at relatively high temperatures. For MgB<sub>2</sub> superconductor with  $T_c = 39$  K,  $J_c$  drops quickly with both field and temperature. The Fe-based superconductors are a new family of high- $T_c$  superconductors and have  $T_c$  as high as 56 K (Ref. 2) and  $B_{c2}$  above 70–80 T,<sup>3</sup> along with small anisotropy of 5–6 for REFeAsO<sub>1-x</sub>F<sub>x</sub> (RE-1111 phase, with RE a rare-earth element),<sup>4</sup> but are almost isotropic for (Ba,K)Fe<sub>2</sub>As<sub>2</sub> (122 phase).<sup>5</sup> These compounds show  $J_c$  over  $1-3 \times 10^5-10^6$  A/cm<sup>2</sup> at 5 K for both  $B//ab$  and  $B//c$ .<sup>6,7</sup> (in thin films and crystals with higher  $J_c$ ). It was also found that grain boundaries are not an important issue in iron pnictide superconductors.<sup>8</sup> These properties make the Fe-based superconductors extremely promising candidates for high magnetic field applications at relatively high temperatures. The current-carrying ability of these superconductors at high fields and temperatures is largely determined by the flux-pinning strength, which is found to be very large, as much as 9100 K in Ba<sub>0.72</sub>K<sub>0.28</sub>Fe<sub>2</sub>As<sub>2</sub> single crystal.<sup>9</sup>

At the irreversibility field,  $H_{irr}$ , vortices start to move along the direction of the current flow, and hence the critical current vanishes. The current-density decay behaviour is governed by the pinning mechanism. The in-field  $J_c$  is mainly controlled by the flux pinning mechanisms. There are two basic pinning mechanisms in type-II superconductors. The first is the pinning due to the randomly distributed spatial variations in the transition temperature  $T_c$ , which is called  $\delta T_c$  pinning. The second pinning mechanism relates to spatial fluctuation of the charge-carrier mean free path, the so called  $\delta l$  pinning, mostly due to crystal lattice defects.<sup>1,10</sup> It has been reported that the  $\delta T_c$  pinning is the main flux pinning mechanism in Pr-doped YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7</sub> (YBCO),<sup>11</sup> and pure MgB<sub>2</sub> bulk and thin films.<sup>12-14</sup> It was reported, however, that  $\delta l$  pinning is the important mechanism in stoichiometric Y-based high- $T_c$  superconducting thin films.<sup>10</sup> It was also found that both mechanisms coexist in the nanoparticle doped-MgB<sub>2</sub> samples, depending on the temperature.<sup>15,16</sup>

Preliminary experimental results indicate that the vortex dynamics in Fe-based superconductors may be understood through the thermally activated flux motion model based on collective vortex pinning.<sup>7,9,17-19</sup> Fluctuation of mean free path and transition temperature induced vortex pinning, however, as the flux pinning mechanism for the Fe-based superconductors has not been studied so far.

In this paper, the vortex pinning mechanisms of Ba<sub>0.72</sub>K<sub>0.28</sub>Fe<sub>2</sub>As<sub>2</sub> single crystal have been studied systematically by magnetization loop measurements at different temperatures. It was found that both the  $\delta l$  and the  $\delta T_c$  pinning mechanisms coexist in the Ba<sub>0.72</sub>K<sub>0.28</sub>Fe<sub>2</sub>As<sub>2</sub> single crystal in fields smaller than 4 T, while the  $\delta l$  pinning mechanism is the only effect at higher magnetic fields. Their contributions are strongly temperature and magnetic field dependent.

The Ba<sub>0.72</sub>K<sub>0.28</sub>Fe<sub>2</sub>As<sub>2</sub> crystals used in the present work were grown using a flux method. High purity elemental Ba, K, Fe, As, and Sn were mixed in a molar ratio of

<sup>a)</sup> Author to whom correspondence should be addressed. Electronic mail: xiaolin@uow.edu.au.

$\text{Ba}_{1-x}\text{K}_x\text{Fe}_2\text{As}_2:\text{Sn} = 1:45\text{--}50$  for the self-flux. A crucible with a lid was used to minimize the evaporation loss of K as well as that of As during growth. The crucible was sealed in a quartz ampoule filled with Ar and loaded into a box furnace. The details of the crystal growth are given in Ref. 20. The as-grown single crystal was cleaved and cut into a rectangular shape for measurements. The transport properties were measured over a wide range of temperature and magnetic fields up to 6 T with applied current of 5 mA using a physical properties measurement system (PPMS, Quantum Design).

Magnetization loops were collected for a  $(\text{Ba,K})\text{Fe}_2\text{As}_2$  single crystal in different magnetic fields, which were perpendicular to the FeAs planes,  $B//c$ , and temperatures down to 5 K. The critical current density  $J_c$  was obtained from the width  $\Delta M$  of the magnetization loop using the Bean model, where for full sample penetration  $J_c = 20\Delta M/Va(1-a/3b)$ , where  $a$  and  $b$  are the width and the length of the sample perpendicular to the applied field, respectively,  $V$  is the sample volume, and  $\Delta M$  is the height of the  $M$ - $H$  hysteresis loop. The resulting  $J_c$  versus applied field is plotted in Fig. 1. At 5 K, the  $J_c$  value is  $3.3 \times 10^5 \text{ A/cm}^2$  at  $B = 2 \text{ T}$ , and it only decreases to  $6.2 \times 10^4 \text{ A/cm}^2$  at  $B = 6 \text{ T}$ . The weak dependence of  $J_c$  on magnetic field and temperature suggests that the  $(\text{Ba,K})\text{Fe}_2\text{As}_2$  single-crystal superconductor has superior  $J_c$  behaviour, which is beneficial for potential applications in high magnetic fields.

The temperature dependence of the normalised  $J_c$  at magnetic fields of 1, 3, 4, and 5 T is presented in Fig. 2. The normalised  $J_c$  has a linear dependence on temperature in the low temperature region and a slight enhancement of the log (normalised  $J_c$ ) in the high temperature region. Actually, similar behaviour was also reported for both single crystal and polycrystalline cuprate superconductors.<sup>11,21</sup> In order to describe the current densities of high- $T_c$  superconductors, Thompson *et al.*<sup>21</sup> explained the temperature dependence of  $J_c$  in the framework of the thermally activated flux motion model and the model of collective flux pinning and creep. They found the following expression for the temperature dependence of  $J_c$ :

$$J_c(T) = \frac{J_{dp}(T)}{\left\{1 + \left[\mu k_B T \ln\left(\frac{t_1}{t_{eff}} + 1\right) / U_c(T)\right]\right\}^{1/\mu}}, \quad (1)$$

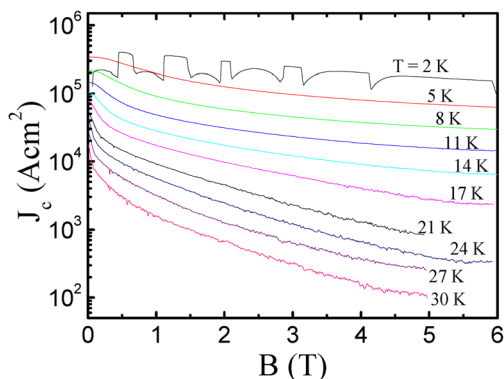


FIG. 1. The  $J_c$ -field dependence obtained from the  $M$ - $H$  loops at different temperatures measured on a  $\text{Ba}_{0.72}\text{K}_{0.28}\text{Fe}_2\text{As}_2$  single crystal.

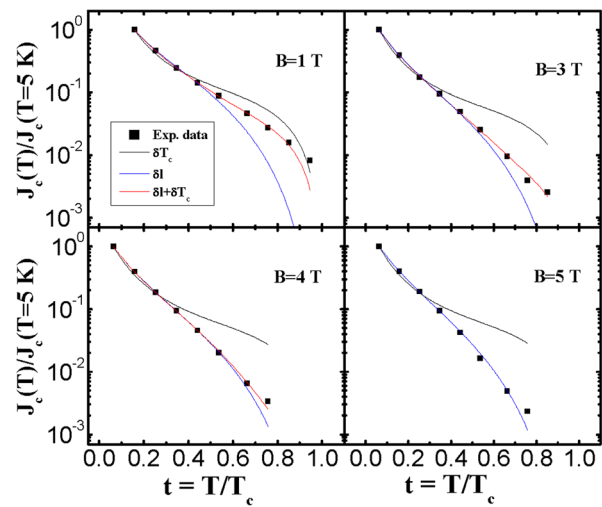


FIG. 2. Temperature dependence of the normalised measured current density  $J_c$  at magnetic fields of 1, 3, 4, and 5 T. The solid lines are the theoretical curves obtained based on the model of the  $\delta l$  (blue curves) pinning mechanism, the model of the  $\delta T_c$  (black curves) pinning mechanism, and the coexistence of both (red curves) pinning mechanisms.

where  $J_{dp}(T)$  is the depinning current density,  $U_c(T)$  is the characteristic pinning potential,  $\mu$  is the glassy exponent,  $t_1$  is the time at which the data was recorded, and  $t_{eff}$  is the effective attempt time for a flux segment/bundle to jump over the potential barrier. The glassy exponent  $\mu$  gives the influence on the current dependence of  $U_c(T)$ , depending on the flux creep regime.<sup>22</sup> By assuming  $U_c(T) = U_c(0)g(t)$  and  $J_{dp}(T) = J_{dp}(0)J(t)$  with  $U_c(0)$ , and  $J_{dp}(0)$  the corresponding values at  $T = 0 \text{ K}$  and  $t = T/T_c$ , the following temperature dependence for  $J_c(T)$  can be obtained:

$$J_c(T) = \frac{J_{dp}(0)J(t)}{\{1 + [\mu k_B T C / g(t)]\}^{1/\mu}} \quad (2)$$

with

$$C = \ln\left(\frac{t_1}{t_{eff}} + 1\right) / U_c(0) \quad (3)$$

which is a temperature independent constant.

In the framework of the collective theory, Griessen *et al.*<sup>10</sup> pointed out that the  $\delta l$  and  $\delta T_c$  pinning mechanisms result in different temperature dependencies of  $J(t)$  and  $g(t)$ . They found:

$$J(t) = (1 - t^2)^{7/6} (1 + t^2)^{5/6}, \quad (4)$$

$$g(t) = (1 - t^2)^{1/3} (1 + t^2)^{5/3}, \quad (5)$$

for  $\delta T_c$  pinning, and

$$J(t) = (1 - t^2)^{5/2} (1 + t^2)^{-1/2}, \quad (6)$$

$$g(t) = 1 - t^4 \quad (7)$$

for  $\delta l$  pinning. One can easily find from Eqs. (1), (4), and (6) that at  $T = 0 \text{ K}$ ,  $J_c(0) = J_{dp}(0)$ , and therefore, we can fit the critical current density data with Eq. (1) by adjusting only



two parameters, i.e.,  $C$  and  $\mu$ . The theoretical curves obtained based on the model of  $\delta l$  (blue curves) and  $\delta T_c$  (black curves) pinning are shown in Fig. 2. At magnetic field lower than 4 T, one can see that the experimentally obtained critical current density value resides in between the  $\delta l$  and  $\delta T_c$  pinning. Therefore, both the  $\delta l$  and the  $\delta T_c$  pinning coexist, while for  $B > 4$  T, the temperature dependence of the  $J_c$  is found to be in excellent agreement with the model of the  $\delta l$  pinning mechanism, and the data cannot be explained by the model of the  $\delta T_c$  pinning.

To investigate further the real pinning mechanism of the  $\text{Ba}_{0.72}\text{K}_{0.28}\text{Fe}_2\text{As}_2$  single crystal samples, the  $J_c(T)$  data were analyzed by assuming the coexistence of both the  $\delta l$  and the  $\delta T_c$  pinning mechanisms within the following expression:

$$J_c(T) = P_1 J_s^l(T) + P_2 J_s^{T_c}(T), \quad (8)$$

where  $J_s^l(T)$  and  $J_s^{T_c}(T)$  are the expression for the  $\delta l$  and the  $\delta T_c$  pinning, respectively.  $P_1$  and  $P_2$  are fitting parameters. The  $J_c(T)$  data were well described by Eq. (8) at magnetic fields lower than 5 T, as shown by the red solid curves in Fig. 2. The best-fitted value of  $\mu$  is  $0.38 \pm 0.01$  for the  $\text{Ba}_{0.72}\text{K}_{0.28}\text{Fe}_2\text{As}_2$  single crystal. The  $\mu$  value is in good agreement with  $\mu = 0.45$ , which was estimated from studies of E-J curves for  $\text{Ba}(\text{Fe}_{1-x}\text{Co}_x)\text{As}_2$  at  $B = 0.5$  T.<sup>19</sup> Therefore, a positive  $\mu$  indicates elastic vortex motion for the  $\text{Ba}_{0.72}\text{K}_{0.28}\text{Fe}_2\text{As}_2$  single crystal. This is because from studies of E-J curves, it was suggested that a negative  $\mu$  value corresponds to plastic vortex motion, while a positive  $\mu$  indicates elastic vortex motion.<sup>20</sup>

The value of  $0.5 \pm 0.1$  was obtained for parameter  $C$ , which is roughly magnetic field independent. This parameter may depend on magnetic field through the  $\ln(t/t_{\text{eff}} + 1)$  factor and the temperature independent pinning potential  $U_c$  in Eq. (3). For the  $\text{Ba}_{0.72}\text{K}_{0.28}\text{Fe}_2\text{As}_2$  single crystal,  $U_0$  is magnetic field independent in the magnetic field range studied here.<sup>9</sup> It was found<sup>21</sup> that  $\ln(t/t_{\text{eff}} + 1) = \ln[2v_0B/a(\text{dB}/\text{dt})]$ , where  $v_0$  is the attempt velocity, which is expected to be field dependent, since single-vortex hopping occurs at low fields, while flux-bundle motion is expected at high fields.  $a$  is the lateral dimension of the sample and  $\text{dB}/\text{dt}$  is the sweep rate of magnetic field  $B$ . Therefore, the variation of  $C$  with magnetic field through the  $\ln(t/t_{\text{eff}} + 1)$  factor is logarithmic and for the field range under examination could be roughly constant.

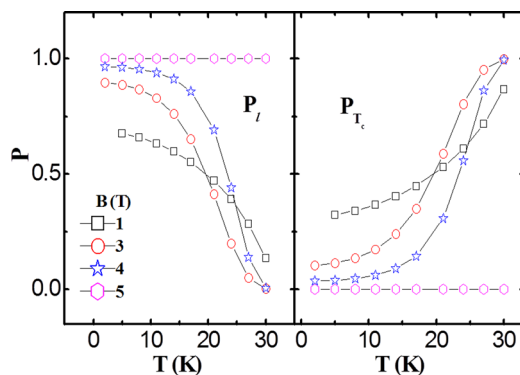


FIG. 3.  $\delta l$  and  $\delta T_c$  pinning contributions as functions of temperature in  $\text{Ba}_{0.72}\text{K}_{0.28}\text{Fe}_2\text{As}_2$  single crystal at different magnetic fields.

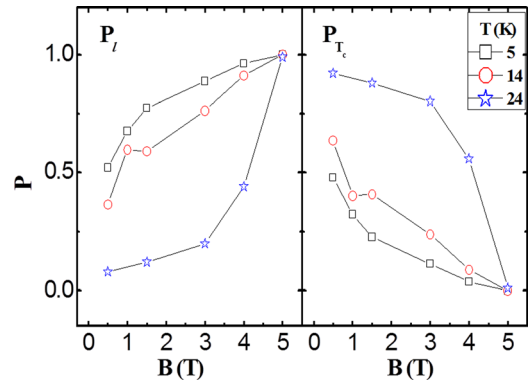


FIG. 4. Magnetic field dependences of the  $\delta l$  and the  $\delta T_c$  pinning contributions in  $\text{Ba}_{0.72}\text{K}_{0.28}\text{Fe}_2\text{As}_2$  single crystal at different temperatures.

In order to compare the effects of the  $\delta l$  and the  $\delta T_c$  pinning mechanisms, the  $P$  parameter was defined as  $P_l = P_1 J_s^l(T)/J_c(T)$  and  $P_{T_c} = P_2 J_s^{T_c}(T)/J_c(T)$ , which represent the  $\delta l$  and the  $\delta T_c$  pinning effects, respectively, with  $P_l + P_{T_c} = 1$ . The results of both pinning effect contributions are shown in Fig. 3. As can be seen in Fig. 3, the pinning mechanism strongly depends on the temperature. Between 20 and 23 K and for  $B \leq 4$  T, the two pinning mechanisms have roughly equal effects, while above these temperatures,  $\delta T_c$  pinning is dominant. For temperatures close to  $T_c$  and  $B \leq 4$  T, the  $T_c$  fluctuation increases, and therefore, the  $\delta l$  pinning is suppressed completely. When the temperature is far below  $T_c$ , the  $T_c$  fluctuation disappears, and the  $\delta l$  pinning is dominant.

The magnetic field dependences of both the  $\delta l$  and the  $\delta T_c$  pinning mechanisms are shown in Fig. 4. Both  $\delta l$  and  $\delta T_c$  pinning coexist at magnetic fields lower than 4 T. The  $\delta l$  pinning is dominant at high magnetic fields and low temperatures; it decreases with decreasing field and increasing temperature, while the  $\delta T_c$  pinning shows the opposite trend up to  $B = 4$  T and is suppressed completely at  $B = 5$  T. Therefore, at higher magnetic field, the  $\delta l$  is the only effective pinning mechanism.

In conclusion, from the temperature dependence of the critical current density within the collective pinning model at different magnetic fields, we have found that the  $\delta l$  pinning due to spatial fluctuations of the charge-carrier mean free path is strongly dominant at low temperature and low magnetic fields in  $\text{Ba}_{0.72}\text{K}_{0.28}\text{Fe}_2\text{As}_2$  single crystal. At temperatures close to the critical temperature, however, there is evidence for the  $\delta T_c$  pinning, while at higher magnetic fields, the  $\delta l$  pinning mechanism is the only effect.

This work was supported by the Australian Research Council through Discovery projects DP1094073 and DP120100095.

<sup>1</sup>G. Blatter, M. V. Feigelman, V. B. Geshkenbein, A. I. Larkin, and V. M. Vinokur, *Rev. Mod. Phys.* **66**, 1125 (1994).

<sup>2</sup>C. Wang, L. Li, S. Chi, Z. Zhu, Z. Ren, Y. Li, Y. Wang, X. Lin, Y. Luo, S. Jiang, X. Xu, G. Cao, and Z. Xu, *Europhys. Lett.* **83**, 67006 (2008).

<sup>3</sup>G. Fuches, S.-L. Drechsler, N. Kozlova, M. Bartkowiak, J. E. Hamann-Borrero, G. Behr, K. Nenkov, H.-H. Klauss, H. Maeter, A. Amato, H. Luetkens, A. Kwadrin, R. Khasanov, J. Freudenberger, A. Köhler, M. Knupfer, E. Arushanov, H. Rosner, B. Buchner, and L. Schultz, *New J. Phys.* **11**, 075007 (2009).

- <sup>4</sup>J. Jaroszynski, F. Hunte, L. Balicas, Y.-J. Jo, I. Raičević, A. Gurevich, D. C. Larbalestier, F. F. Balakirev, L. Fang, P. Cheng, Y. Jia, and H. H. Wen, *Phys. Rev. B* **78**, 174523 (2008).
- <sup>5</sup>H. Q. Yuan, J. Singleton, F. F. Balakirev, S. A. Baily, G. F. Chen, J. L. Luo, and N. L. Wang, *Nature (London)* **457**, 565 (2009).
- <sup>6</sup>N. Ni, M. E. Tillman, J.-Q. Yan, A. Kracher, S. T. Hannahs, S. L. Bud'ko, and P. C. Canfield, *Phys. Rev. B* **78**, 214515 (2008).
- <sup>7</sup>H. Yang, C. Ren, L. Shan, and H. H. Wen, *Phys. Rev. B* **78**, 092504 (2008).
- <sup>8</sup>T. Katase, Y. Ishimaru, A. Tsukamoto, H. Hiramatsu, T. Kamiya, K. Tanabe, and H. Hosono, *Nature Commun.* **2**, 409 (2011).
- <sup>9</sup>X. L. Wang, S. R. Ghorbani, S.-I. Lee, S. X. Dou, C. T. Lin, T. H. Johansen, K.-H. Müller, Z. X. Cheng, G. Peleckis, M. Shabazi, A. J. Quiller, V. V. Yurchenko, G. L. Sun, and D. L. Sun, *Phys. Rev. B* **82**, 024525 (2010).
- <sup>10</sup>R. Griessen, Wen Hai-hu, A. J. J. van Dalen, B. Dam, J. Rector, H. G. Schnack, S. Libbrecht, E. Osquiguil, and Y. Bruynseraede, *Phys. Rev. Lett.* **72**, 1910 (1994).
- <sup>11</sup>H. H. Wen, Z. X. Zhao, Y. G. Xiao, B. Yin, and J. W. Li, *Physica C* **251**, 371 (1995).
- <sup>12</sup>M. J. Qin, X. L. Wang, H. K. Liu, and S. X. Dou, *Phys. Rev. B* **65**, 132508 (2002).
- <sup>13</sup>C. Buzea and T. Yamashita, *Supercond. Sci. Technol.* **14**, R115 (2001).
- <sup>14</sup>D. K. Finnemore, J. E. Ostenson, S. L. Bud'ko, G. Lapertot, and P. C. Canfield, *Phys. Rev. Lett.* **86**, 2420 (2001).
- <sup>15</sup>S. R. Ghorbani, X. L. Wang, S. X. Dou, Sung-Ik Lee, and M. S. A. Hossain, *Phys. Rev. B* **78**, 184502 (2008).
- <sup>16</sup>S. R. Ghorbani, X. L. Wang, M. S. A. Hossain, S. X. Dou, and Sung-Ik Lee, *Supercond. Sci. Technol.* **23**, 025019 (2010).
- <sup>17</sup>H. Yang, H. Q. Luo, Z. S. Wang, and H. H. Wen, *Appl. Phys. Lett.* **93**, 142506 (2008).
- <sup>18</sup>R. Prozorov, N. Ni, M. A. Tanatar, V. G. Kogan, R. T. Gordon, C. Martin, E. C. Blomberg, P. Proumapan, J. Q. Yan, S. L. Bud'ko, and P. C. Canfield, *Phys. Rev. B* **78**, 224506 (2008).
- <sup>19</sup>R. Prozorov, M. A. Tanatar, E. C. Blomberg, P. Proumapan, R. T. Gordon, N. Ni, S. L. Bud'ko, and P. C. Canfield, *Physica C* **469**, 667 (2009).
- <sup>20</sup>G. L. Sun, D. L. Sun, M. Konuma, P. Popovich, A. Boris, J. B. Peng, K.-Y. Choi, P. Lemmens, and C. T. Lin, *J. Supercond. Novel Magn.* **24**, 1773 (2011).
- <sup>21</sup>J. R. Thompson, Yang Ren Sun, L. Civale, A. P. Malozemoff, M. W. McElfresh, A. D. Marwick, and F. Holtzberg, *Phys. Rev. B* **47**, 14440 (1993).
- <sup>22</sup>M. V. Feigel'man, V. B. Geshkenbein, A. I. Larkin, and V. M. Vinokur, *Phys. Rev. Lett.* **63**, 2303 (1989).