

2003

## Magnetic shielding in MgB<sub>2</sub>/Fe superconducting wires

J. Horvat

*University of Wollongong*, [jhorvat@uow.edu.au](mailto:jhorvat@uow.edu.au)

Saeid Soltanian

*University of Wollongong*, [saeid@uow.edu.au](mailto:saeid@uow.edu.au)

Xiaolin Wang

*University of Wollongong*, [xiaolin@uow.edu.au](mailto:xiaolin@uow.edu.au)

S. X. Dou

*University of Wollongong*, [shi@uow.edu.au](mailto:shi@uow.edu.au)

Follow this and additional works at: <https://ro.uow.edu.au/engpapers>



Part of the [Engineering Commons](#)

<https://ro.uow.edu.au/engpapers/1>

---

### Recommended Citation

Horvat, J.; Soltanian, Saeid; Wang, Xiaolin; and Dou, S. X.: Magnetic shielding in MgB<sub>2</sub>/Fe superconducting wires 2003.

<https://ro.uow.edu.au/engpapers/1>

# Magnetic Shielding in MgB<sub>2</sub>/Fe Superconducting Wires

J. Horvat, S. Soltanian, X. L. Wang, and S. X. Dou

**Abstract**—Transport critical current ( $I_c$ ) was measured for MgB<sub>2</sub>/Fe round wires, with the magnetic field oriented perpendicular to the wire and parallel to it. Measurements were made on a wire with a pure MgB<sub>2</sub> core and another wire where the MgB<sub>2</sub> core was doped with nano-size SiC. This doping strongly improved the vortex pinning in MgB<sub>2</sub>. The field dependence of  $I_c$  was strongly improved due to the presence of the iron sheath. At 30 K,  $I_c$  did not depend on the field for fields between 0.09 and 0.7 T. At lower temperatures,  $I_c$  increased with the field, after an initial decrease, resembling a “peak effect.” This effect was extended to higher fields as the temperature was decreased: at 10 K the peak appeared at 3.5 T. This improvement was not due to mere magnetic shielding by iron, but more likely to an interaction between the iron sheath and the superconductor. Improvement of vortex pinning did not affect the range of fields within which this effect was observed.  $J_c$  of SiC doped MgB<sub>2</sub>/Fe wires at elevated fields already satisfies the requirements for their use in production of superconducting magnets for particle accelerators.

**Index Terms**—Critical current, magnetic shielding, MgB<sub>2</sub>/Fe superconducting wires.

## I. INTRODUCTION

THE MgB<sub>2</sub> superconductor is a new candidate for making superconducting wires that can be used without the need for liquid helium. Its relatively high critical temperature of 39 K makes it possible to use it at 20 K, a temperature readily available with modern cryo-coolers. Quite early in the development of MgB<sub>2</sub> wires, it became clear that iron is one of the best materials for use as a sheath for the wires [1]–[4]. Transport critical current density ( $J_c$ ) of  $1.3 \times 10^5$  A/cm<sup>2</sup> was obtained at 20 K and 1.7 T for the samples measured here. In addition to providing a medium for obtaining MgB<sub>2</sub> in the chemical reaction at high temperature and ensuring the mechanical strength of the wires, iron is a ferromagnetic material that can be utilized to magnetically shield the superconductor from the external field. This could be very effectively employed for decoupling the superconducting filaments in a multifilamentary MgB<sub>2</sub>/Fe wire, substantially lowering the AC loss in the wires.

Our first results on the influence of an iron sheath on the field dependence of transport  $J_c$  revealed a much better improvement of  $J_c$  than expected from mere magnetic shielding [5]. There was a range of fields where  $J_c$  did not change with field. This was attributed to the interaction between the superconductor and iron sheath, because it was measured at high fields, for which

the magnetic shielding was no longer effective. This range of fields was found to widen with decreasing temperature, indicating that it may be possible to obtain a very weak field dependence of  $J_c$  at 20 K, at high fields. However, the lowest temperature at which the measurements could be performed was 32 K, which was limited by the maximum current available from the pulse current source. Here, we used an improved current source, enabling measurements at temperatures less than 20 K. Improving the vortex pinning by newly discovered nano-SiC doping [6], we also test how the vortex pinning affects the superconductor/sheath interaction.

## II. EXPERIMENTAL PROCEDURE

Superconducting wires were prepared by filling an iron tube with a mixture of 99% pure powders of magnesium and boron. For one of the wires, 10 wt.% of amorphous nano-size SiC was added. The wires were drawn to a diameter of 1.4 mm, with the diameter of the inner core of 0.8 mm. Heating in flowing argon to 800 °C for 15 minutes, MgB<sub>2</sub> was formed in a chemical reaction. As shown recently, addition of SiC strongly improves the vortex pinning of MgB<sub>2</sub>, resulting in much improved field dependence of the critical current density ( $J_c$ ) [6]. The details of the wire preparation can be found elsewhere [7]. The wires measured had the same outer diameter and diameter of superconducting core. The sheath was made from the same iron tube for all the wires, ensuring the magnetic properties of the sheath were the same for all the samples measured.

Because critical current for these wires was hundreds of amperes, the transport measurements had to be performed by a pulse-method to avoid heating. A pulse of current was obtained by discharging a capacitor through the sample, coil of thick copper wire and noninductive resistor connected in series. The current was measured via the voltage drop on the noninductive resistor of 0.01 Ohm. With a proper choice of the coil, the current reached its maximum value (700 A) within 1 ms. The voltage developed on the sample was measured simultaneously with the current, using a 2-channel digital oscilloscope. Because both channels of the oscilloscope had the same ground, the signal from the voltage taps was first fed to a transformer preamplifier (SR554). This decoupled the voltage taps from the resistor used for measuring the current, thereby avoiding creation of ground loops and parasitic voltages in the system, as well as of an additional current path in parallel with the sample. The transformer amplified the voltage 100 times, improving the sensitivity of the experiment. The reliability of this experimental set-up was checked by measuring the resistance of a copper wire with this method and a dc method, using the same current- and

Manuscript received August 6, 2002. This work was supported by the Australian Research Council and Hyper Tec Research Inc., OH, USA.

The authors are with the Institute for Superconducting and Electronic Materials, University of Wollongong, NSW 2522, Australia (e-mail: jhorvat@uow.edu.au).

Digital Object Identifier 10.1109/TASC.2003.812303

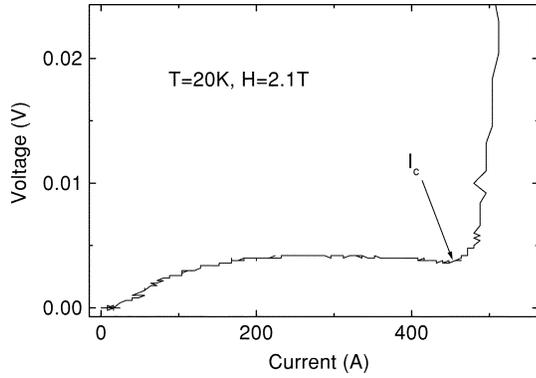


Fig. 1. A typical voltage-current characteristic for MgB<sub>2</sub>/Fe wire obtained by the pulse-method.

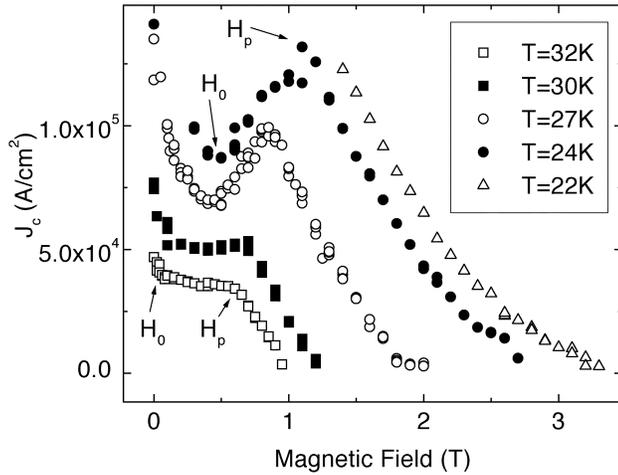


Fig. 2. Field dependence of  $J_c$  for an undoped MgB<sub>2</sub> wire with field perpendicular to the wire.

voltage-contacts. The measured resistance was the same within 1.7%.

A typical  $V-I$  characteristic is shown in Fig. 1. Self-field of the current pulse induced a voltage in the voltage taps, which gave a background voltage. This voltage increased gradually at the beginning of the pulse, but was almost constant for most of the pulse duration (Fig. 1). It was easy to distinguish the voltage created by the superconductor on this background, because the voltage developed very abruptly when the current reached the value of  $I_c$ .

The magnetic field was produced by a 12 T superconducting magnet. Sample mounting allowed for orienting the field either perpendicular to the wire, or parallel to it. In the latter case, the field was also parallel to the current passing through the sample. The sample was placed into a continuous flow helium cryostat, allowing the control of temperature to better than 0.1 K.

### III. EXPERIMENTAL RESULTS

Fig. 2 shows the field dependence of  $J_c$  for a nondoped wire at  $T = 32, 30, 27, 24$  and  $22$  K. For all the temperatures, there is an initial decrease of  $J_c$  with the field, up to a field  $H_0$ . After the decrease,  $J_c$  is almost independent of the field at  $T = 30$  and  $32$  K, up to a value of field  $H_p$ . For  $H > H_p$ ,  $J_c$  decreases with  $H$  exponentially. For lower temperatures,  $J_c$  starts increasing

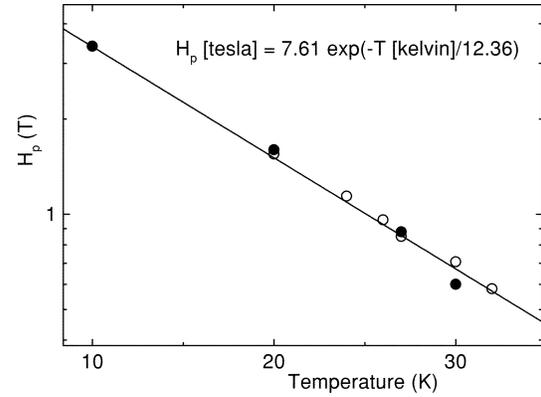


Fig. 3. Temperature dependence of  $H_p$  for undoped (open symbols) and SiC doped (solid symbols) MgB<sub>2</sub>/Fe wires. Solid line is the fit with (1).

with the field for  $H > H_0$ , giving a field dependence of  $J_c$  resembling a “peak effect” (Fig. 2).  $J_c$  peaks at  $H = H_p$  and it decreases exponentially with field for  $H > H_p$  (Fig. 2). The occurrence of the plateau and peak in  $J_c$  vs.  $H$  improves the field dependence of  $J_c$ , as shown previously for  $T > 30$  K [5]. This was shown to occur because of the interaction between the Fe sheath and superconductor. The field range with improved  $J_c$  widens with decreasing temperature. For lower temperatures, the critical current at low fields was higher than the maximum current available with our experimental set-up, and the peak could not be measured. Qualitatively the same results were also obtained for the SiC doped wire, which had improved field dependence of  $J_c$  for  $H > H_p$ .

To study the temperature dependence of the field range with improved  $J_c$ ,  $H_p$  is plotted as a function of temperature in Fig. 3. It should be noted that  $J_c$  is improved by Fe sheath even for fields higher than  $H_p$  for  $T < 30$  K (Fig. 2), however there is no clear feature in  $J_c$  vs.  $H$  for  $H > H_p$  to enable a clear distinction of the field range with improved  $J_c$ . As shown in Fig. 3,  $H_p$  decreases with temperature exponentially:

$$H_p [\text{tesla}] = 7.61 \exp\left(-\frac{T [\text{kelvin}]}{12.36}\right). \quad (1)$$

The temperature dependence of  $H_p$  is shown in Fig. 3 by solid and open symbols for pure and SiC doped wires, respectively. Apparently, improvement of vortex pinning by doping does not affect the values of  $H_p$ .

Fig. 4 shows the field dependence of  $J_c$  for a pure MgB<sub>2</sub>/Fe wire at 30 K with field parallel to the wire (open symbols), as compared to the field perpendicular to the wire (solid symbols). As opposed to the perpendicular field,  $J_c$  for the parallel field initially increases with the field, up to a field  $H_1$ . This is followed by an exponential decrease of  $J_c$  with field for  $H > H_1$ . At lower temperatures (below 27 K),  $J_c$  is almost constant for  $H < H_1$ . The value of  $H_1$  decreases with temperature as:  $H_1 = 3303 \text{ Tesla} \exp(-T/3 \text{ Kelvin})$  (Fig. 5), much faster than  $H_p$ .

### IV. DISCUSSION

The plateau in the field dependence of  $J_c$  has been reported earlier for MgB<sub>2</sub>/Fe wires, for  $T > 30$  K [5]. The plateau

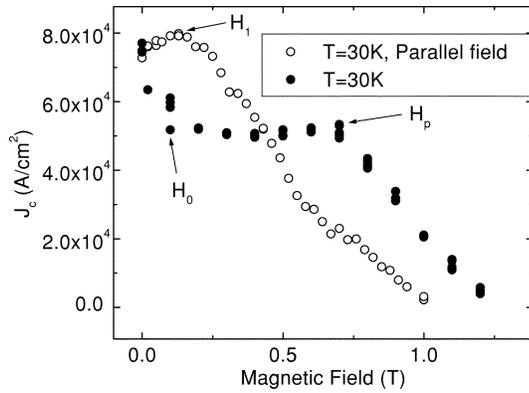


Fig. 4. Field dependence of  $J_c$  for an undoped  $\text{MgB}_2/\text{Fe}$  wire at 30 K, with field perpendicular (solid symbols) and parallel (open symbols) to the wire.

was observed to widen with decreasing temperature. It was suggested that the plateau occurred as a consequence of the interaction between the superconductor and the iron sheath. In this work, we investigated the temperature dependence of the plateau for  $T < 30$  K, thanks to an improved pulse current source enabling measurements of higher values of  $I_c$ .

The plateau was observed for  $T > 30$  K in this work, as well. However, instead of the plateau, an increase of  $J_c$  with  $H$  was observed for  $T < 30$  K, resulting in a peak in the field dependence of  $J_c$  (Fig. 2). The peak apparently develops from the plateau as the temperature decreases, because the temperature dependence of  $H_p$  follows the same exponential law for  $T > 30$  K and  $T < 30$  K. Measurements of magnetic shielding of hollow Fe cylinder showed that the shielding is effective up to about 0.2 T [5]. The effectiveness of the shielding should not vary strongly at temperatures between 20 and 32 K, because the Curie temperature of iron is much higher than this. Apparently, it is the change of superconducting properties of the  $\text{MgB}_2$  core that is responsible for the exponential decrease of  $H_p$  with  $T$ . Because of this, strong improvement of vortex pinning with SiC doping was expected to affect the temperature dependence of  $H_p$ . To our surprise, this did not occur (Fig. 3).

The field dependence of  $J_c$  with the field parallel to the wire is also influenced by the iron sheath. It was shown earlier that there is a plateau in  $J_c(H)$  for  $H < 0.02$  T and  $T = 32$  K [5]. This was interpreted as simple magnetic shielding of the iron sheath. Namely, measurements of the field inside the shield for the parallel field showed that the internal field was almost zero and constant for  $H < 0.02$  T. All of the field in excess to 0.02 T penetrated the iron sheath for this field configuration. Here, we show that for  $T < 32$  K,  $J_c$  slightly increases with the field (Fig. 4) and the field range in which this occurs ( $H < H_1$ ) increases strongly with decreasing temperature (Fig. 5). The field dependence of  $H_1$  is actually much stronger than that of  $H_p$ . In addition, it was shown earlier that the magnetic shielding for the parallel field is very weak [5]. Again, such strong temperature dependence of  $H_1$  cannot be ascribed to simple magnetic shielding. Apparently, the interaction between the superconducting core and iron sheath is responsible for the anomalous improvement of the field dependence of  $J_c$  for both parallel and perpendicular field.

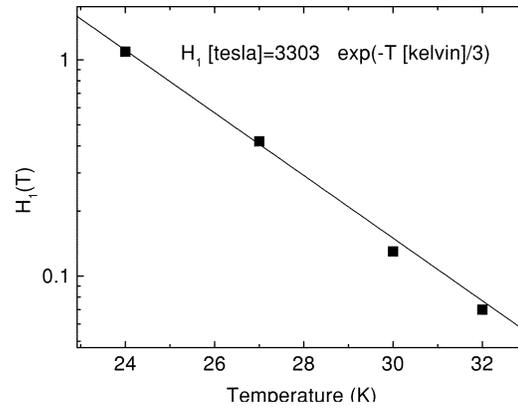


Fig. 5. Temperature dependence of  $H_1$  for an undoped  $\text{MgB}_2/\text{Fe}$  wire with field parallel to the wire. Solid line is the fit with the exponential function.

Improvement of critical current of a superconductor via interaction with its magnetic surrounding was studied theoretically by Genenko *et al.* [8]. In their model, critical currents were calculated for type II superconducting thin strips in partly filled vortex state in a magnetic surrounding. Only self-field of the transport current was considered, and the magnetic surrounding was supposed to be reversible, linear and homogeneous. They considered the influence of the magnetic surrounding on the current distribution in the central vortex-free part of the strip. The current distribution was found to be very sensitive to the shape of the magnetic surrounding and its distance to the strip. They predicted an increase of the maximum loss-free current by a factor of 100 when a superconducting strip is placed in an open magnetic cavity. However, for the smallest practically achievable distance between the superconductor and magnetic surrounding of 0.1 mm, the maximum loss-free current is predicted to be 7 times larger than the critical current without the magnetic surrounding. This increase of the apparent critical current occurs because of distribution of the current into the vortex-free region of the superconducting strip, whilst the vortices are confined to the edges of the strip. So far, no experiments have been reported to verify this model.

In the model of Genenko *et al.* [8], the vortices were confined to the edges of a thin superconducting strip by edge barriers. The model also considered the case of a partly flux filled thick superconducting strip with weak edge barriers and strong vortex pinning. Vortex pinning defined the critical current, according to the critical state model [9]. However, due to the pinning, the transport current is confined to the edges of the superconductor where there is a constant gradient in the density of magnetic vortices defined by the pinning, and  $J_c$  is constant. Therefore, vortex distribution for strong pinning with weak edge barriers is similar to the case of edge barriers with weak pinning. The magnetic surrounding causes a distribution of the transport current into the flux free region of the superconductor, similar to the case of weak pinning with edge barriers. This results in a loss-free current density exceeding the critical current defined by the critical state model [8]. Because of this, we expected to observe a change in the value of  $H_p$  with improvement of the pinning by SiC doping, because the flux profile in the superconductor changes with the change of the vortex pinning. However, no change in  $H_p$  was observed (Fig. 3).

The reason we did not observe the change in  $H_p$  with SiC doping may be that the model was devised only for the self-field, whereas in our experiment we used an additional external field. The geometry of our sample (round wire) was also not the same as the one in the model (strip). Because the model did not consider the case of external field, it is not clear if the change of the pinning should result in a change of  $H_p$  in the model (even though intuitively, one would expect this to occur).

There is also a possibility that  $H_p$  is a parameter that does not reflect the change of vortex pinning. Actual mechanisms for the occurrence of the peak effect are not known and the meaning of  $H_p$  is consequently not clear. Preliminary results of further research indicate that there are other characteristic fields associated with the occurrence of the peak effect, too<sup>1</sup>. Additionally, the magnetization state of the iron shield affects the peak effect, even though this does not seem to be the mechanism for its occurrence.<sup>1</sup>

## V. CONCLUSION

It was found that, instead of the expected plateau in the field dependence of  $J_c$ , the value of  $J_c$  increases with field at low temperatures, resembling a peak effect. The field of the peak in  $J_c(H)$  increases exponentially with decreasing temperature. Thanks to the peak, the value of  $J_c$  at 20 K and 1.7 T is almost the same as the zero-field  $J_c$  at that temperature, of the order of  $10^5$  A/cm<sup>2</sup>. At still lower temperatures, the peak extends to higher fields, reaching 3.5 T at 10 K. Even though its exact origin is still not clear, this effect can be employed for

<sup>1</sup>Measurements are still under way. The results are expected to be published in 2003.

improvement of the field dependence of  $J_c$  of MgB<sub>2</sub> wires. It has already pushed the field performance of  $J_c$  (as measured by pulsed current method) of SiC doped MgB<sub>2</sub>/Fe wires at 20 K beyond the minimum requirements needed for production of the magnets employed in particle accelerators [10].

## REFERENCES

- [1] S. Soltanian, X. L. Wang, I. Kusevic, E. Babic, A. H. Li, M. J. Qin, J. Horvat, H. K. Liu, E. W. Collings, E. Lee, M. D. Sumption, and S. X. Dou, "High-transport critical current density above 30 K in pure Fe-clad MgB<sub>2</sub> tape," *Phys. C*, vol. 361, pp. 84–90, 2001.
- [2] S. Jin, H. Mavoori, C. Bower, and R. B. van Dover, *Nature*, vol. 411, p. 563, 2001.
- [3] C. Beneduce, H. L. Suo, P. Toulemonde, N. Musolino, and R. Flükiger, "Transport critical current, anisotropy, irreversibility fields and exponential  $n$  factors in Fe sheathed MgB<sub>2</sub> tapes," cond-mat/0203551, submitted for publication.
- [4] W. Goldacker, S. I. Schlachter, H. Reiner, S. Zimmer, B. Obst, H. Kiesel, and A. Nyilas, "Mechanically reinforced MgB<sub>2</sub> wires and tapes with high transport currents," in *Studies of High-Temperature Superconductors*, A. Narlikar, Ed. New York: Nova Science Publishers, 2002, vol. 45, to be published.
- [5] J. Horvat, X. L. Wang, S. Soltanian, and S. X. Dou, "Improvement of critical current in MgB<sub>2</sub> superconducting wires by a ferromagnetic sheath," *Appl. Phys. Lett.*, vol. 80, no. 5, pp. 829–831, Feb. 2002.
- [6] S. X. Dou, S. Soltanian, J. Horvat, X. L. Wang, P. Munroe, S. H. Zhou, M. Ionescu, H. K. Liu, and M. Tomsic, "Enhancement of the critical current density and flux pinning of MgB<sub>2</sub> superconductor by nanoparticle SiC doping," *Appl. Phys. Lett.*, vol. 81, pp. 3419–3421, 2002.
- [7] X. L. Wang, S. Soltanian, J. Horvat, A. H. Liu, M. J. Qin, H. K. Liu, and S. X. Dou, "Very fast formation of superconducting MgB<sub>2</sub>/Fe wires with high  $J_c$ ," *Phys. C*, vol. 361, pp. 141–155, 2001.
- [8] Yu, A. Genenko, A. Snezhko, and H. C. Freyhardt, "Overcritical states of a superconductor strip in a magnetic environment," *Phys. Rev. B*, vol. 62, pp. 3453–3471, 2000.
- [9] C. P. Bean, "Magnetization of high-field superconductors," *Rev. Mod. Phys.*, vol. 35, pp. 31–39, Jan. 1964.
- [10] E. W. Collings, private communication, Aug. 2002.