



UNIVERSITY
OF WOLLONGONG
AUSTRALIA

University of Wollongong
Research Online

Australian Institute for Innovative Materials - Papers

Australian Institute for Innovative Materials

2016

Thermoelectric signals of state transition in polycrystalline SmB₆

Zengji Yue

University of Wollongong, zy709@uowmail.edu.au

Q.J. Chen

Hunan University

Xiaolin Wang

University of Wollongong, xiaolin@uow.edu.au

Publication Details

Yue, Z. J., Chen, Q. J. & Wang, X. L. (2016). Thermoelectric signals of state transition in polycrystalline SmB₆. *Journal of Physics: Condensed Matter*, 28 (35), 355801-1-355801-4.

Research Online is the open access institutional repository for the University of Wollongong. For further information contact the UOW Library:
research-pubs@uow.edu.au

Thermoelectric signals of state transition in polycrystalline SmB6

Abstract

Topological Kondo insulator SmB6 has attracted quite a lot of attention from the condensed matter physics community. A number of unique electronic properties, including low-temperature resistivity anomaly, 1D electronic transport and 2D Fermi surfaces have been observed in SmB6. Here, we report on thermoelectric transport properties of polycrystalline SmB6 over a broad temperature from 300 to 2 K. An anomalous transition in the temperature-dependent Seebeck coefficient S from $S(T) \propto T^{-1}$ to $S(T) \propto T$ was observed around 12 K. Such a transition demonstrates a transition of conductivity from 3D metallic bulk states to 2D metallic surface states with insulating bulk states. Our results suggest that the thermotransport measurements could be used for the characterization of state transition in topological insulators.

Disciplines

Engineering | Physical Sciences and Mathematics

Publication Details

Yue, Z. J., Chen, Q. J. & Wang, X. L. (2016). Thermoelectric signals of state transition in polycrystalline SmB6. *Journal of Physics: Condensed Matter*, 28 (35), 355801-1-355801-4.

Thermoelectric signals of state transition in polycrystalline SmB₆

Z. J. Yue^{1a)}, Q. J. Chen², C. Zhang¹ and X. L. Wang¹

1. Institute for Superconducting and Electronic Materials, Faculty of Engineering, University of Wollongong, North Wollongong, NSW 2500, Australia

2. School of Physics and Electronics, Hunan University, Changsha 410082, China

Topological Kondo insulator SmB₆ has attracted quite a lot of attentions from condensed matter physics community. A number of unique electronic properties, including low-temperature resistivity anomaly, 1D electronic transport and 2D Fermi surfaces have been observed in SmB₆. Here, we report on thermoelectric transport properties of polycrystalline SmB₆ over a broad temperature from 300 K to 2 K. An anomalous transition in the temperature-dependent Seebeck coefficient S from $S(T) \propto T^{-1}$ to $S(T) \propto T$ was observed around 12 K. Such a transition demonstrates a transition of conductivity from 3D metallic bulk states to 2D metallic surface states with insulating bulk states. Our results suggest that the thermotransport measurements could be used for the characterization of state transition in topological insulators.

Key words: Topological Kondo insulators, SmB₆, Seebeck effects, State transition.

PACS numbers: 72.20.Pa, 73.20.At

Topological insulators are quantum matters with topologically protected metallic surface states and insulating bulk states.¹ Fascinating electronic properties, including the quantum spin Hall effects, exotic Majorana particles, and topological magnetoelectric effects have been observed in topological insulators.² With these novel properties, they hold high promising for next generation spintronics and quantum computing. Topological Kondo insulator SmB₆ that is a well-known strong correlated and heavy fermion system has recently attracted quite a lot of attentions from this field.³ Various experimental measurements have been utilized to investigate the topological surface states in SmB₆ single crystals, which include magneto-transport, angle-resolved photoemission spectroscopy (ARPES), torque magnetometry and quantum oscillation.^{3,4,5} Many unique electronic properties, including

truly bulk-insulating, low-temperature resistivity anomaly, possible nematic phase, 1D edge state transport, and 2D unconventional Fermi surfaces have been observed in SmB_6 .^{3,4,6,7}

On the other hand, most discovered topological insulator materials, including Bi_2Se_3 , Bi_2Te_3 and Sb_2Te_3 , demonstrate high bulk conductivity due to defects induced bulk carriers.⁸ In these topological insulators, the surface transport can be masked by highly conductive bulk states.⁹ In contrast, in the SmB_6 , the surface transport is dominant in low temperature due to truly insulating bulk states. There are large amounts of grain boundaries in polycrystalline SmB_6 . These boundaries could form 2D surface states and conductivity channels in low temperature. Here, we report on thermoelectric transport measurements in polycrystalline SmB_6 and demonstrate a state transition from Seebeck effect. The Seebeck coefficient displays an anomalous transition from $S(T) \propto T^{-1}$ to $S(T) \propto T$ around 12 K. Such a transition suggests a transition of conductivity from 3D metallic bulk states to 2D metallic surface states with insulating bulk states. In addition, our results provide evidences that topological surface states exist and is robust to large amounts of boundaries and defects in the polycrystalline SmB_6 .

Polycrystalline samples of SmB_6 were fabricated in a vacuum furnace at a high temperature of 900 °C and a high pressure of 7 bar. The SmB_6 samples are in the shape of bars with typical dimensions of about $2 \times 2 \times 10 \text{ mm}^3$. The Seebeck coefficient, electrical resistivity, and thermal conductivity were measured using a Quantum Design 14 T Physical Properties Measurement System (PPMS). The four-probe mode was employed in thermoelectric transport measurements between 2 K and 300 K. The applied AC bias current was 2 mA.

Figure 1(a) shows the temperature dependent resistivity of polycrystalline SmB_6 in the range from 2K to 300 K. Above 40 K, the bulk Kondo gap is closed due to thermal energy excitations, and the SmB_6 behaves like a metal. As the temperature decreases, the resistivity increases by several orders of magnitude due to the opening of a Kondo gap. Below 3.5 K, the resistivity approaches a constant value of $\sim 0.017 \Omega\cdot\text{m}$, which originates from the surface states of SmB_6 .⁶ In Figure 1(b), the Hall resistance is plotted as a function of magnetic fields at different temperatures. The negative sign in the Hall effect demonstrates that the carriers are electrons at low temperatures. The calculated carrier density in polycrystalline SmB_6 are

about $3.25 \times 10^{18} \text{ cm}^{-3}$ and $1.5 \text{ cm}^2/\text{V}\cdot\text{s}$, respectively. Compared to SmB_6 single crystals, the mobility is quite low.¹⁰ This is attributable to very high density of boundaries and defects in the polycrystalline SmB_6 . Fig. 1(c) and (d) presents the magnetization as a function of temperature and magnetic fields, respectively. The polycrystalline SmB_6 demonstrates paramagnetic behaviour at high temperature. The low temperature Curie tail maybe related to the recent observed surface ferromagnetic domain walls.⁷

Figure 2(a) shows the total thermal conductivity, κ , decreases with the temperature decreasing. A subtle transition of the κ happens at $\sim 40 \text{ K}$ which corresponds to an opening of the Kondo gap. As the Kondo gap (hybridization gap) opens, the contribution to the κ from electrons decreases. The thermal conductivity is the sum of two contributions of electrons and phonons, which can be expressed as $\kappa = \kappa_e + \kappa_p$. At low temperatures, the reduced dimensions from 3D bulk states to 2D surface states reduces the electron contribution. At high temperature, large κ stems from high density of bulk electrons with strong correlated interactions.

Fig. 2(b) shows the Seebeck coefficient, S , as a function of the temperature. A dramatically low-temperature peak of S was seen at $\sim 12 \text{ K}$. The low temperature value of the S peak is $-324 \mu\text{VK}^{-1}$. Below 3.5 K , S is linearly dependent on temperature. We find that the S as a function of the temperature in SmB_6 represents a 3D bulk value at higher temperature with the relation $S(T) \propto T^1$. With the temperature decreasing, the relation changes to $S(T) \propto T$ below a critical temperature. In this temperature range, the dominant carriers are electrons from 2D surface states.

Above 12 K , the Seebeck coefficient S arises from the electronic contribution in the 3D SmB_6 bulk. Based on the Boltzman equation and the Mott relation, the Seebeck coefficient is described as,¹¹

$$\mathbf{S} = -\frac{1}{eT} \frac{\int L(\epsilon)(\epsilon-u) \left(-\frac{\partial f}{\partial \epsilon}\right) d\epsilon}{\int L(\epsilon) \left(-\frac{\partial f}{\partial \epsilon}\right) d\epsilon} \quad (1)$$

Here, $L(\epsilon) = \rho_c(\epsilon)v_c(\epsilon)^2\tau_c(\epsilon)$, where $\rho_c(\epsilon)$ is density of states, $v_c(\epsilon)$ is the electron velocity, $\tau_c(\epsilon)$ is the electron relaxation time, and u is the chemical potential.

The formula yields the well known Seebeck coefficient for semiconductors,

$$S(T) \approx -\frac{k_B}{e} \frac{E_{c,v}-u}{k_B T} \quad (2)$$

here $E_{c,v}$ is the gap edge position of the conduction or valence band, and k_B is Boltzmann's constant. Assuming that $\frac{du}{dT}$ is negligible, S is proportional to $-\frac{1}{k_B T}$ at high temperature.

$$\text{Hence, } S(T) \propto -\frac{1}{T} \quad (3)$$

S is sensitive to the characteristics of the electronic structure. According to ARPES, the band structures of SmB₆ display a Kondo gap of about 15 meV at the Fermi level and surface states below 15 K.¹² The 2D metallic surface states also emerge below 15 K. Below $T = 12$ K, the Seebeck coefficient S arises from the electronic contribution in the metallic surface states. R. Takahashi *et al.* have theoretically studied thermoelectric transport in 3D topological insulators by the Boltzmann equation. In a 2D topological insulator, the transport matrix for describing thermoelectric transport is,¹³

$$\begin{pmatrix} j/q \\ w \end{pmatrix} = \begin{pmatrix} L_0 & L_1 \\ L_1 & L_2 \end{pmatrix} \begin{pmatrix} -\frac{du}{dx} \\ -\frac{1}{T} \frac{du}{dx} \end{pmatrix} \quad (4)$$

Here, j is the electric current induced by electric field and w is the thermal current induced by thermal gradient. q is charge, and u is the chemical potential.

From the matrix elements, the thermoelectric parameters can be expressed as,

$$\sigma = e^2 L_0 \quad (5)$$

$$S = -\frac{1}{eT} \frac{L_1}{L_0} \quad (6)$$

$$k_e = \frac{1}{T} \frac{L_0 L_2 - L_1^2}{L_0} \quad (7)$$

$$ZT = \frac{L_1^2}{L_0 L_2 - L_1^2 + k_L T L_0} \quad (8)$$

Here, the k_e and k_L is the thermal conductivity from electrons and phonons, respectively, σ is the electrical conductivity, and ZT is the thermoelectric figure of merit. In this theory, k_L is a constant. Considering a thin slab of 3D topological insulator with a small thickness d , so that the bulk is treated as 2D, from the Boltzmann transport equation, the surface state transport can be expressed as,

$$L_v = c(\mathbf{k}_B \mathbf{T})^v \int_{-\tilde{\Delta}}^0 \frac{(x-\tilde{u})_0 e^{-x+\tilde{u}}}{(e^{-x+\tilde{u}+1})^2} dx \quad (9)$$

$$c = \frac{1}{\pi L_y} \frac{\hbar v^2}{n_i V^2(0)} \quad (10)$$

$$\tilde{u} = \frac{u}{k_B T} \text{ and } \tilde{\Delta} = \frac{\Delta}{k_B T} \quad (11)$$

Here v is the Dirac velocity, V is the average impurity potential, and n_i is the density of impurities.

Hence,

$$\mathbf{S} = -\frac{1}{eT} \frac{L_1}{L_0} \quad (12)$$

$$\mathbf{S}(T) = -\frac{k_B}{e} \frac{\int_{-\tilde{\Delta}}^0 \frac{(x-\tilde{u}) e^{-x+\tilde{u}}}{(e^{-x+\tilde{u}+1})^2} dx}{\int_{-\tilde{\Delta}}^0 \frac{e^{-x+\tilde{u}}}{(e^{-x+\tilde{u}+1})^2} dx} \quad (13)$$

$$\mathbf{S}(T) \propto -T \quad (14)$$

S. P. Chao *et al.* have calculated the thermoelectric transport in the surface states of topological insulators in the presence of randomly distributed impurities.¹⁴ They deduced the generalized Mott formula for S when the temperature is close to zero, $T \rightarrow 0$,

$$S_{ij} = -\frac{\pi^2 k_B^2 T}{3e} \sum_m [\sigma^{-1}]_{im} [\partial \sigma / \partial u]_{mj} \quad (15)$$

Here, σ is the electrical conductivity,

When the impurity potential $V \neq 0$ and the chemical potential $u \approx 0$, $S \propto -\frac{k_B T}{u}$.

For a clean surface state with $V \approx 0$, the density of impurities $n \approx 0$,

$$S_{xx} \approx -\frac{\pi^2 k_B}{3e} \left(\frac{1}{u/k_B T} - \frac{\partial u \Im \Sigma(u)}{\Im \Sigma(u)/k_B T} \right) \quad (16)$$

Combined with Eq. (4), so

$$S \approx -\frac{\pi^2 k_B^2 T}{3ue} \quad (17)$$

Hence, overall, as $T \rightarrow 0$, $S(T) \propto -T$. The final Seebeck becomes

$$\mathbf{S} = -\frac{1}{eT} \frac{L_1}{L_0} \quad (18)$$

As shown in Fig. 2(b), polycrystalline SmB₆ exhibits a low-temperature S anomaly. Below 12 K, $|S|$ decreases linearly with temperature and resembles values for metal-like transport. High-resolution ARPES identified that in-gap low-lying states form electron-like Fermi surface pockets within a 4 meV window of the Fermi level.⁵ They disappear above 15 K, in correspondence with the complete disappearance of the 2D conductivity channels. Hence, the S anomaly below 12 K in polycrystalline SmB₆ is attributable to the 2D conductivity channels.

The efficiency of thermoelectric materials for cooling or power generation is described by the thermoelectric figure of merit ZT

$$ZT = \frac{S^2 \sigma}{\kappa} T \quad (19)$$

where σ , S , and κ are the electrical conductivity, the Seebeck coefficient, and the thermal conductivity respectively. The resulting ZT in polycrystalline SmB₆ is shown in Fig. 3. At high temperature, the 3D metallic bulk transport is dominant. The ZT increases with decreasing temperature and reaches a maximum value of up to 0.0073 at 37 K. Below 37 K, the ZT monotonously decreases down to near zero. Although someone reported that topological surface states could provide a route to optimize the ZT , it is evident that SmB₆ is not promising to be used in thermoelectric devices.^{15,16}

In summary, we report the thermoelectric transport in the polycrystalline topological Kondo insulator SmB₆. We find that the robust surface states survive in polycrystalline material with a large amount of non-magnetic impurities and disorder. The temperature dependent Seebeck coefficient demonstrates an anomalous transition from $S(T) \propto -1/T$ to $S(T) \propto -T$ at 12 K, where surface states start dominating the conductivity. This anomalous transition demonstrates a transformation from 3D metallic bulk states to completely 2D metallic surface states. Our results provide a new way to detect surface states in topological insulators.

Acknowledgements

This work is partially supported by the Australian Research Council under a Discovery project (ARC Discovery, DP130102956).

^{a)} Author to whom correspondence should be addressed. Electronic mail:

zy709@uowmail.edu.au.

References

- ¹ M. Z. Hasan and C. L. Kane, *Reviews of Modern Physics* 82 (4), 3045 (2010).
- ² X.-L. Qi and S.-C. Zhang, *Reviews of Modern Physics* 83 (4), 1057 (2011).
- ³ G. Li, Z. Xiang, F. Yu, T. Asaba, B. Lawson, P. Cai, C. Tinsman, A. Berkley, S. Wolgast, Y. S. Eo, D.-J. Kim, C. Kurdak, J. W. Allen, K. Sun, X. H. Chen, Y. Y. Wang, Z. Fisk, and L. Li, *Science* 346 (6214), 1208 (2014); B. S. Tan, Y.-T. Hsu, B. Zeng, M. C. Hatnean, N. Harrison, Z. Zhu, M. Hartstein, M. Kiourlappou, A. Srivastava, M. D. Johannes, T. P. Murphy, J.-H. Park, L. Balicas, G. G. Lonzarich, G. Balakrishnan, and S. E. Sebastian, *Science* (2015).
- ⁴ Z. Yue, X. Wang, D. Wang, J. Wang, D. Culcer, and S. Dou, *Journal of the Physical Society of Japan* 84 (4), 044717 (2015).
- ⁵ M. Neupane, N. Alidoust, S. Y. Xu, T. Kondo, Y. Ishida, D. J. Kim, C. Liu, I. Belopolski, Y. J. Jo, T. R. Chang, H. T. Jeng, T. Durakiewicz, L. Balicas, H. Lin, A. Bansil, S. Shin, Z. Fisk, and M. Z. Hasan, *Nat Commun* 4 (2013).
- ⁶ D. J. Kim, J. Xia, and Z. Fisk, *Nat Mater* 13 (5), 466 (2014).
- ⁷ Y. Nakajima, P. Syers, X. Wang, R. Wang, and J. Paglione, *Nat Phys* advance online publication (2015).
- ⁸ Y. Ando, *Journal of the Physical Society of Japan* 82 (10), 102001 (2013).
- ⁹ Z. J. Yue, C. B. Zhu, S. X. Dou, and X. L. Wang, *Physical Review B* 86 (19), 195120 (2012); Z. J. Yue, X. L. Wang, and S. X. Dou, *Applied Physics Letters* 101 (15), 152107 (2012).
- ¹⁰ D. J. Kim, S. Thomas, T. Grant, J. Botimer, Z. Fisk, and J. Xia, *Sci. Rep.* 3 (2013).
- ¹¹ G. D. Mahan, in *Solid State Physics*, edited by Henry Ehrenreich and Spaepen Frans (Academic Press, 1997), Vol. Volume 51, pp. 81; M. Cutler and N. F. Mott, *Physical Review* 181 (3), 1336 (1969).
- ¹² J. Jiang, S. Li, T. Zhang, Z. Sun, F. Chen, Z. R. Ye, M. Xu, Q. Q. Ge, S. Y. Tan, X. H. Niu, M. Xia, B. P. Xie, Y. F. Li, X. H. Chen, H. H. Wen, and D. L. Feng, *Nat Commun* 4 (2013).
- ¹³ R. Takahashi and S. Murakami, *Semiconductor Science and Technology* 27 (12), 124005 (2012).
- ¹⁴ S.-P. Chao and V. Aji, *Physical Review B* 84 (15), 155430 (2011).
- ¹⁵ R. Takahashi and S. Murakami, *Physical Review B* 81 (16), 161302 (2010).
- ¹⁶ P. Ghaemi, R. S. K. Mong, and J. E. Moore, *Physical Review Letters* 105 (16), 166603 (2010).

Figures

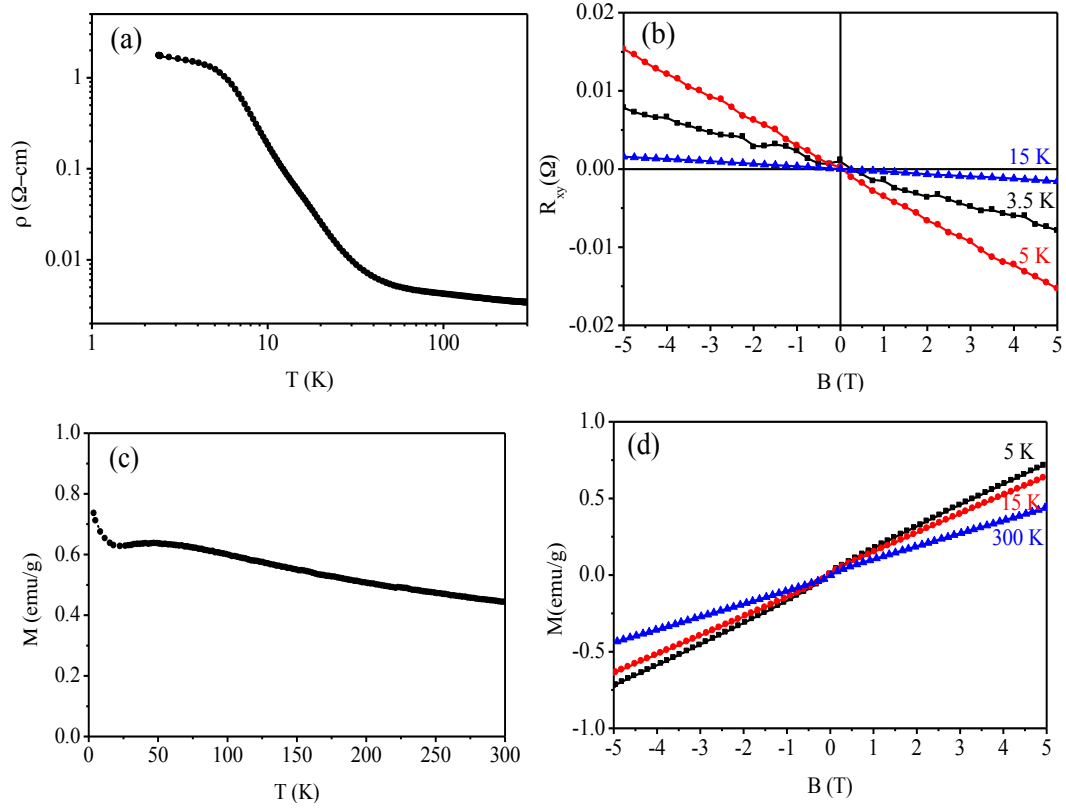


FIG. 1 (a) Resistivity of polycrystalline SmB₆ as function of temperature. (b) Hall resistance of polycrystalline SmB₆ as a function of external magnetic fields. (c) Magnetization of polycrystalline SmB₆ as a function of temperature. (d) Magnetization of polycrystalline SmB₆ as a function external magnetic fields.

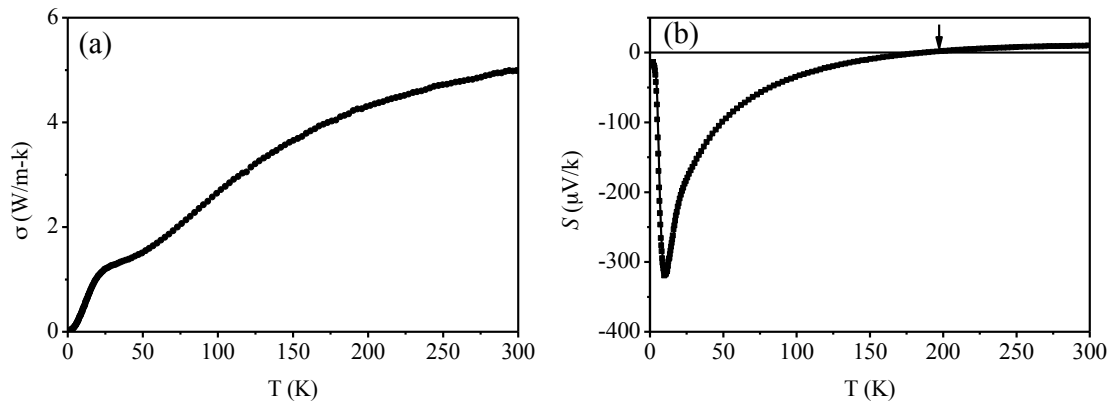


FIG. 2 (a) Thermal conductivity of polycrystalline SmB₆ as functions of temperature. (b) Seebeck coefficient of polycrystalline SmB₆ as functions of temperature.

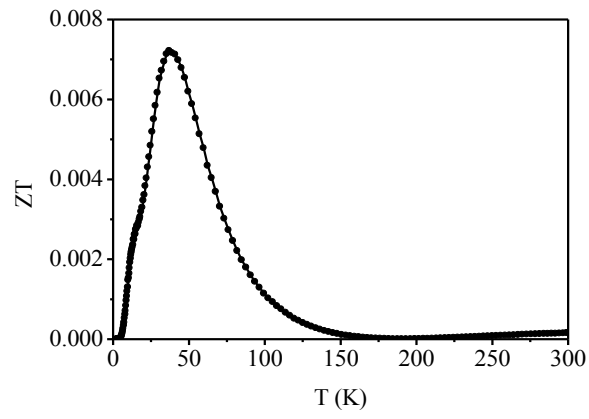


FIG. 3 ZT of polycrystalline SmB_6 as function of temperature.