

January 2005

## **Measurements of the surface diffusion coefficient in iron-carbon alloys using Focused Ion Beam milling and High Temperature Laser Scanning Confocal Microscopy**

D. Blundell

*University of Wollongong, danielb@uow.edu.au*

Mark H. Reid

*University of Wollongong, mreid@uow.edu.au*

N. Zapuskalov

*Cooparoo, Queensland, Australia*

Rian J. Dippenaar

*University of Wollongong, rian@uow.edu.au*

Follow this and additional works at: <https://ro.uow.edu.au/engpapers>

 Part of the [Engineering Commons](#)

<https://ro.uow.edu.au/engpapers/314>

---

### **Recommended Citation**

Blundell, D.; Reid, Mark H.; Zapuskalov, N.; and Dippenaar, Rian J.: Measurements of the surface diffusion coefficient in iron-carbon alloys using Focused Ion Beam milling and High Temperature Laser Scanning Confocal Microscopy 2005.

<https://ro.uow.edu.au/engpapers/314>

## Measurements of the surface diffusion coefficient in iron-carbon alloys using Focused Ion Beam milling and High Temperature Laser Scanning Confocal Microscopy

D. Blundell\*, M. Reid\*, N. Zapuskalov\*\* and R. Dippenaar\*

\*Faculty of Engineering, University of Wollongong, Northfields Avenue, Wollongong NSW, Australia 2522

\*\*Consultant, Coorparoo, Queensland, Australia

The use of high-temperature confocal microscopy, shows a great potential as a means of measuring surface diffusion coefficients in metallic systems[1]. This new experimental approach has an advantage as contaminants entering the system are significantly reduced. Surface diffusion coefficients can be determined at temperatures approaching the melting point.


Mullins and King[2-5] have shown that surface undulations can be related to the surface diffusion coefficient of a metal. In this study, focused ion beam (FIB) milling has been used to introduce geometrically well-defined undulations on the surface of iron and iron carbon alloys (see **figure 1 A**). High temperature laser scanning confocal microscopy was then used to observe the decay *in situ* in real time (**figure 1 B**).

The confocal microscope scans the surface giving a surface-amplitude and width scale. The surface undulations and amplitude are observed to decay at various rates (**figure 2 A**). When the groove width broadening with respect to time is plotted for a given temperature the surface diffusion coefficient can be determined as in **figure 2 B**. The diffusion coefficient  $D_s$  can be derived from the


equation  $w = 6.9Bt^{1/4}$ , where  $t$  is the time in seconds and  $B = \frac{D_s \gamma \Omega^{4/3}}{kT}$ . Here,  $\gamma$  is the surface energy of iron,  $\Omega$  is the atomic volume of iron in the lattice,  $T$  is the temperature and  $k$  is Boltzmann's constant.

The high temperature furnace in the confocal microscope operates in an inert atmosphere and a very low oxygen partial pressure is maintained. This technique rendered surface diffusion rates for carbon steel to be of the order  $10^{-10} \text{ m}^2\text{s}^{-1}$ , compared to  $10^{-8} \text{ m}^2\text{s}^{-1}$  for pure iron above the eutectoid temperature.

1. Zapuskalov, N. and R. Dippenaar. *In-situ observation of microtopography of metal surface at elevated temperature*. in *The Brimacombe Memorial Symposium Poster Proceedings*. 2000. Vancouver, British Columbia, Canada: METSOC.
2. Mullins, W., *Theory of thermal grooving*. J. Appl. Phys., 1956. **28**: p. 333.
3. Mullins, W., *Theory of thermal grooving*. J. Appl. Phys., 1957. **28**: p. 333.
4. Mullins, W., *Flattening of a nearly plain solid surface due to capillarity*. J. Appl. Phys., 1959. **30**: p. 77.
5. King, R. and W. Mullins, *Theory of a surface scratch to flatness*. Acta. Metall., 1962. **10**: p. 601.

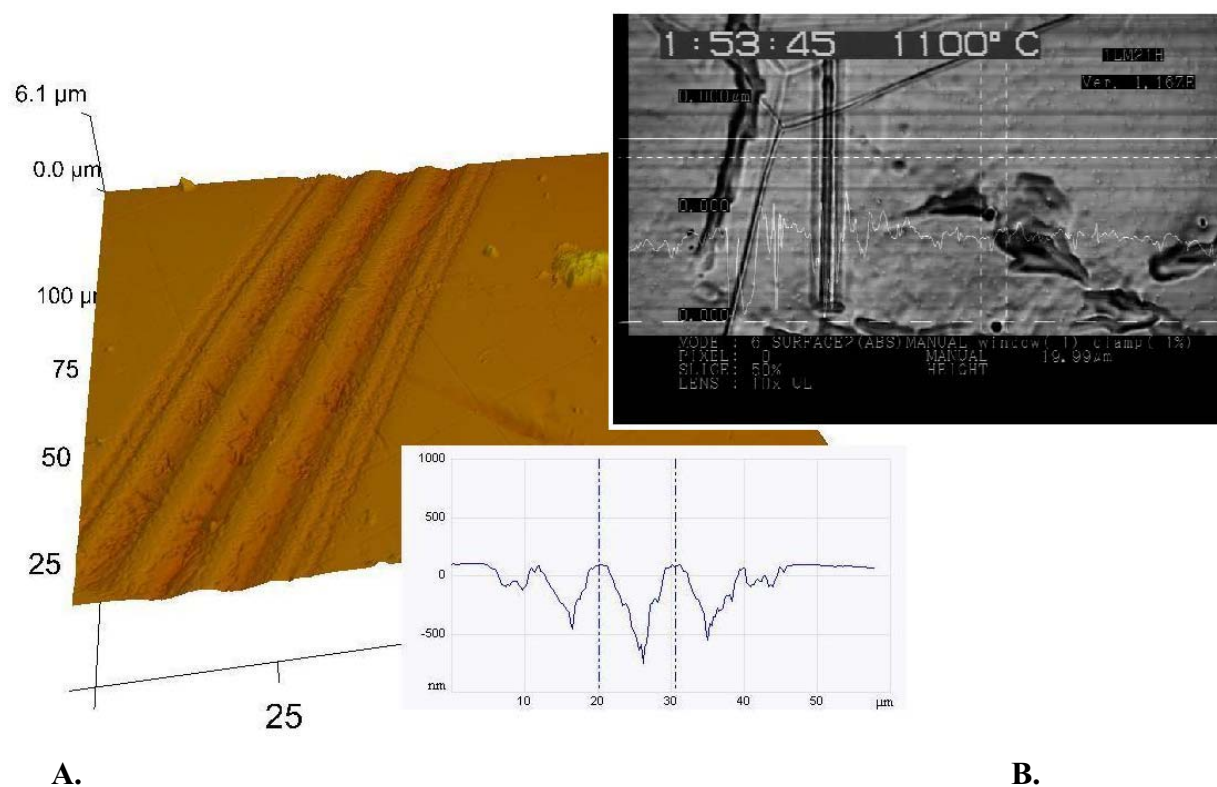

**Figure 1:** (A) A 3D AFM image of a surface groove created in the focused ion beam mill. Inserted is a section view of the depth. (B) The confocal microscope image of the surface showing the scope trace of the groove.

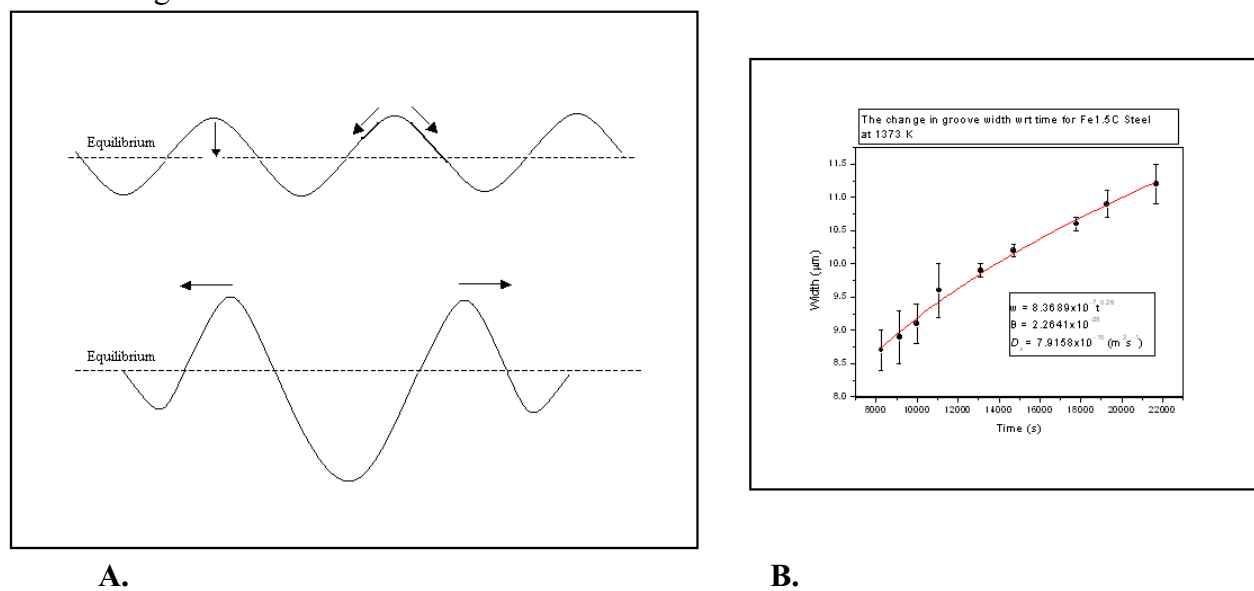

**Figure 2:** (A) A schematic representation of a surface groove decaying. (B) A graph of the groove width decay with respect to time.